

Quantum Dots – Seeds of Nanoscience



KUNGL.
VETENSKAPS-
AKADEMIEN

THE ROYAL SWEDISH ACADEMY OF SCIENCES

THE NOBEL PRIZE IN CHEMISTRY 2023

The Royal Swedish Academy of Sciences has decided to award the Nobel Prize in Chemistry 2023 to

Moungi G. Bawendi

Massachusetts Institute of Technology (MIT),
Cambridge, MA, USA




Louis E. Brus

Columbia University, New York, NY, USA



Alexei I. Ekimov

Nanocrystals Technology Inc., New York,
NY, USA

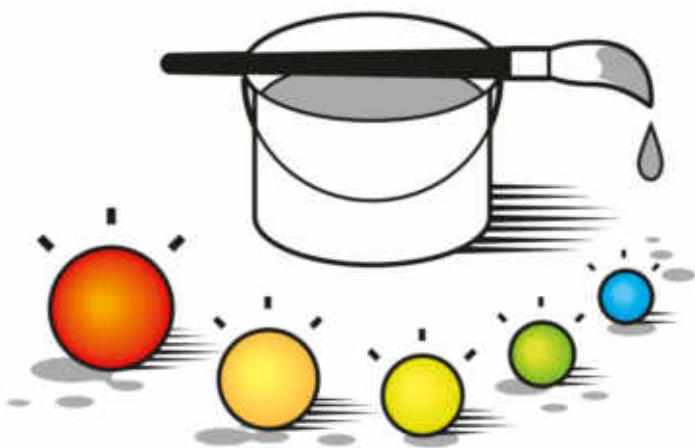

© Johan Jarnestad/The Royal Swedish Academy of Sciences

‘for the discovery and synthesis of quantum dots’

How small are these 'Quantum Dots'?



A quantum dot is a crystal that often consists of just a few thousand atoms. In terms of size, it has the same relationship to a football as a football has to the size of the Earth.



Michael Faraday – Divided metals

Lord Kelvin – Melting depends on size?



Richard Feynman, Nobel Prize 1965 –
Plenty of room at the bottom

Robert F. Curl, Harold W. Kroto and Richard E. Smalley Nobel Prize 1996



Andre Geim and Konstantin Novoselov,
Graphene, Nobel Prize 2010

Jean Pierre Sauvage, J. Fraser Stoddart, and Bernard Lucas Feringa, Molecular machines
Nobel Prize 2016




Faraday, 1857



Faraday's gold preserved in Royal Institution. From the site,
<http://www.rigb.org/rimain/heritage/faradaypage.jsp>

Quantum effects arise when particles shrink

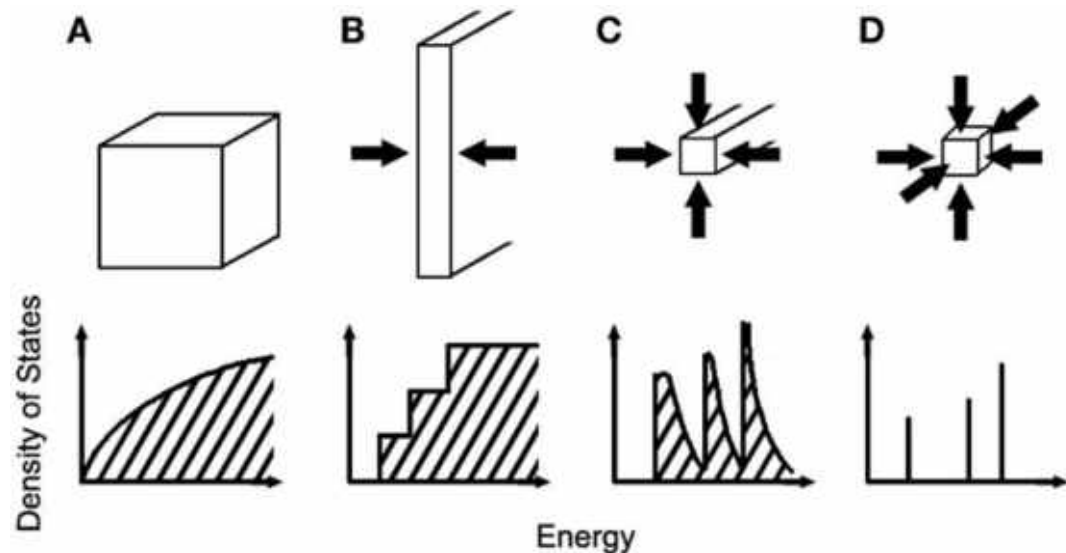

Energy levels of semiconductor crystallites with different dimensionalities.


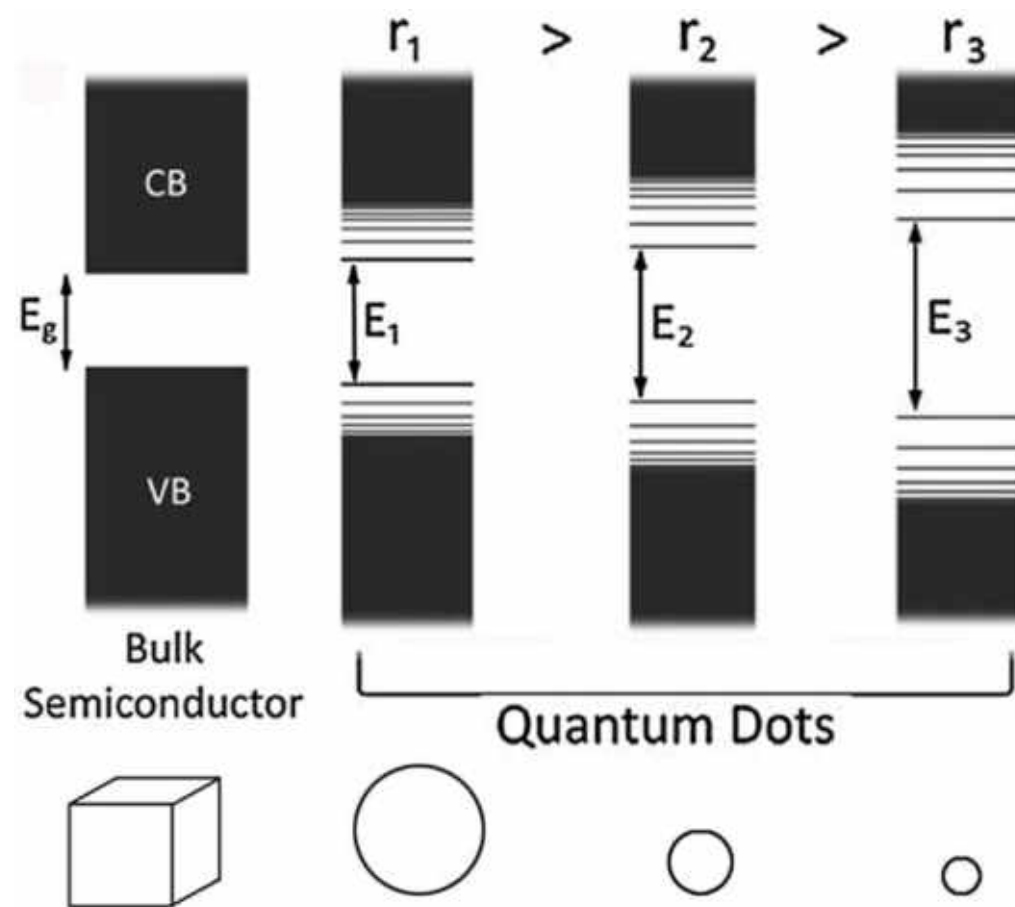


Illustration of size-dependent bandgap.

Illustration of quantum dots

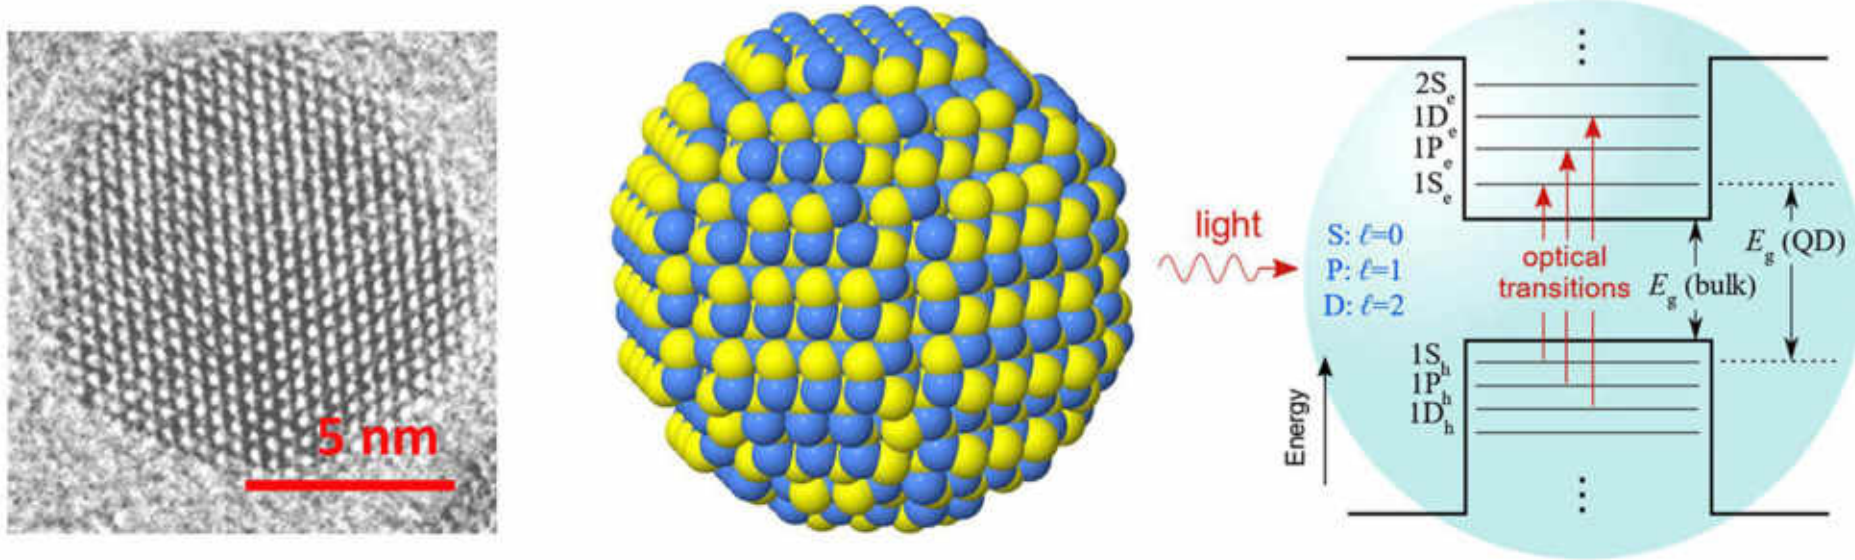

Left: transmission electron microscope image of a CdSe nanocrystal. Centre: Atomic structure of a nanocrystal. Right: Electronic states in a core-shell quantum dot, with the dot itself in the centre bracketed by a wide-bandgap shell.

A. L. Efros and L.E. Brus, ACS Nano 15, 6192 (2021).

Today, ‘quantum dot’ refers to a nanostructure in which quantum mechanical effects manifest themselves in the electronic structure.

- Either through quantum size effects, many-body interactions (excitonic states) or high surface-to-volume ratio such that surface states dominate the electronic structure.
- In addition to a small size comparable to the carriers’ de Broglie wavelength, it is now recognized that the quantum phase coherence length (typically limited by inelastic scattering) needs to exceed the system size.




Silicon dioxide in Lycurgus cup = 73%
Silicon dioxide in Modern Glass = 70%
Sodium oxide in Lycurgus cup = 14%
Sodium oxide in Modern Glass = 15%
Calcium oxide in Lycurgus cup = 7%
Calcium oxide in Modern Glass = 10%


So why is it coloured? The glass contains very small amounts of gold (about 40 parts per million) and silver (about 300 parts per million)

Lycurgus cup; in transmitting light (left) and in reflected light (right). From the site, <http://www.thebritishmuseum.ac.uk>.


'They added colour to nanotechnology'

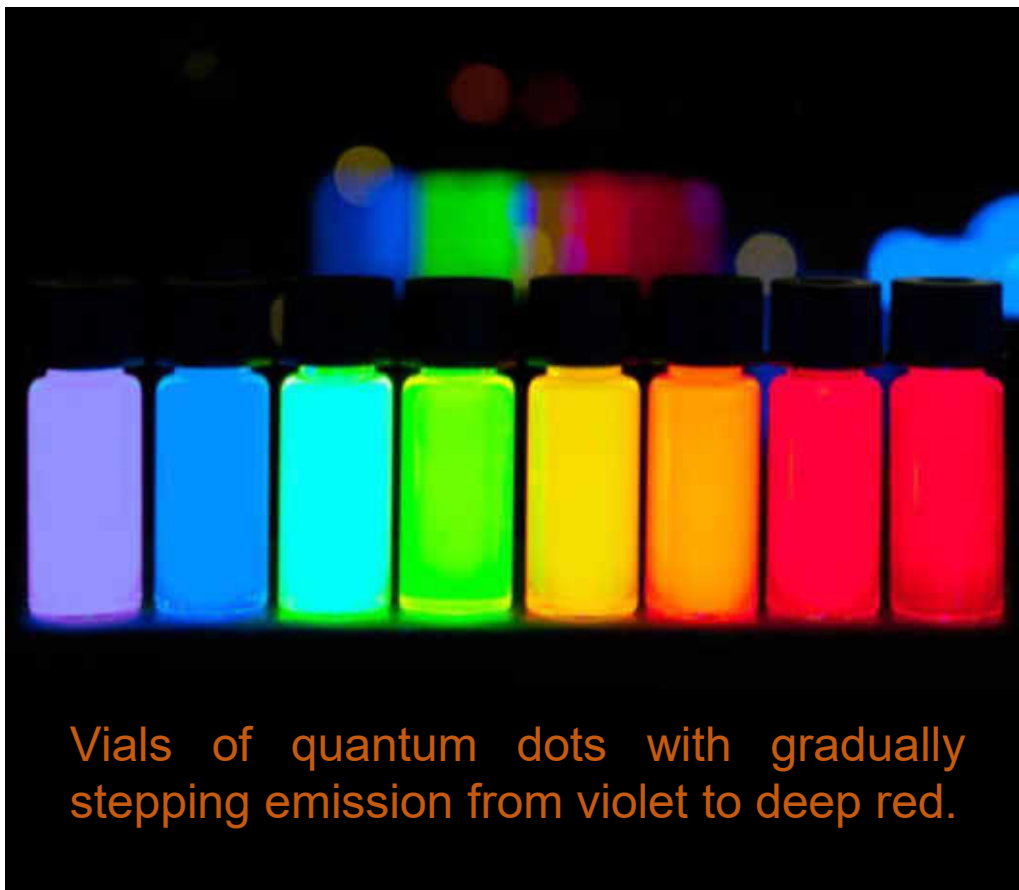


Vials of quantum dots with gradually stepping emission from violet to deep red.

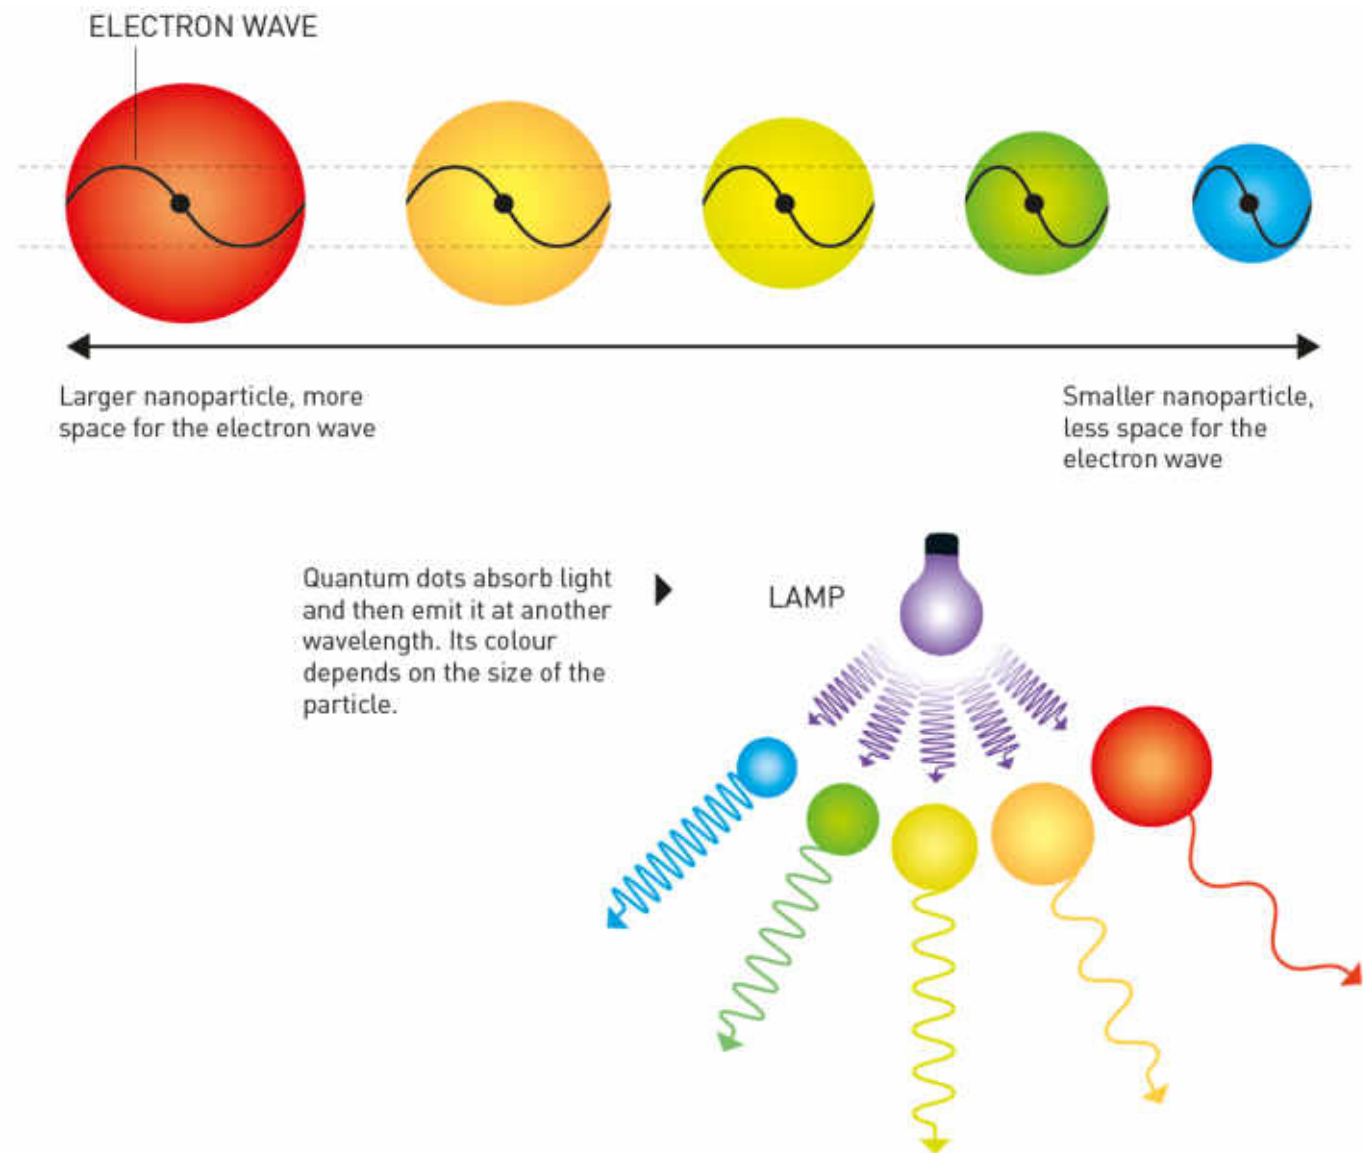

Technology is about manipulating objects

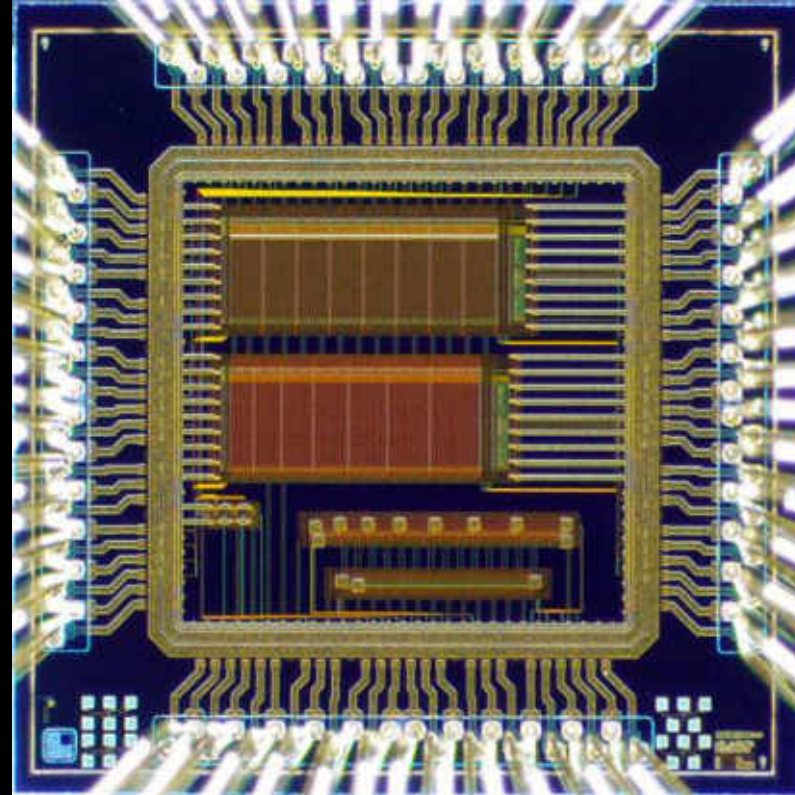


Growth of civilization reduced the size of objects manipulated

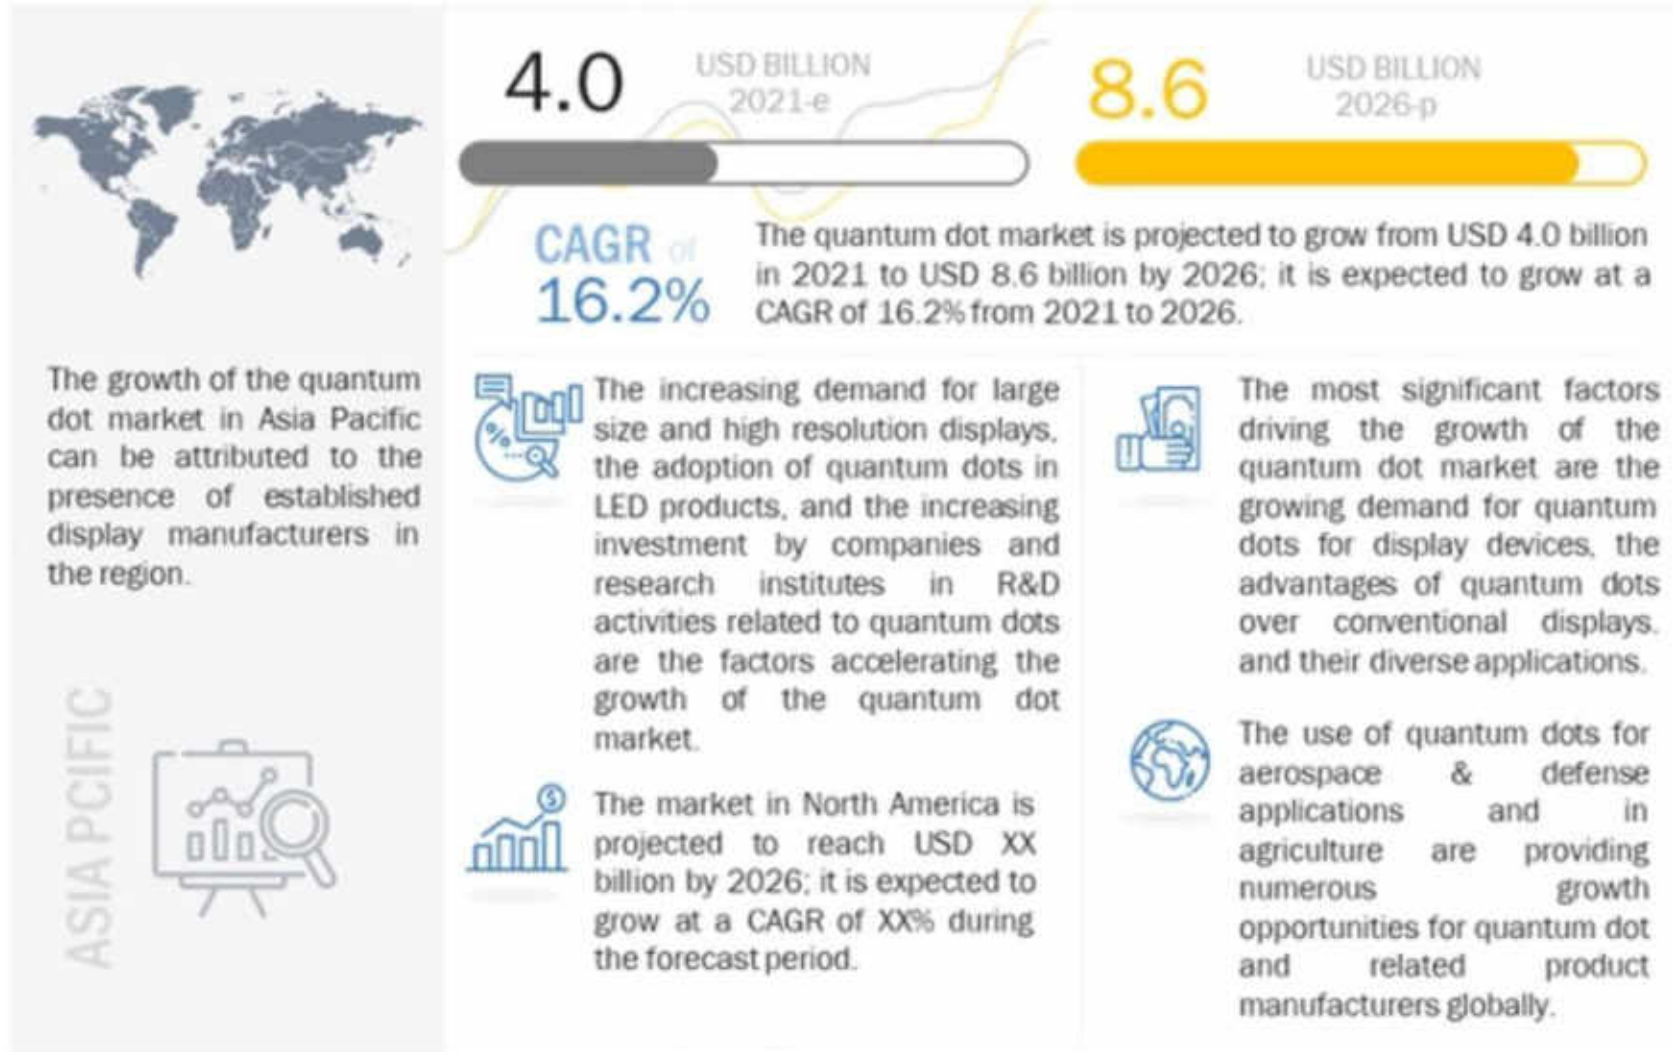


Quantum dot (QLED) displays


QLED Panel Layers

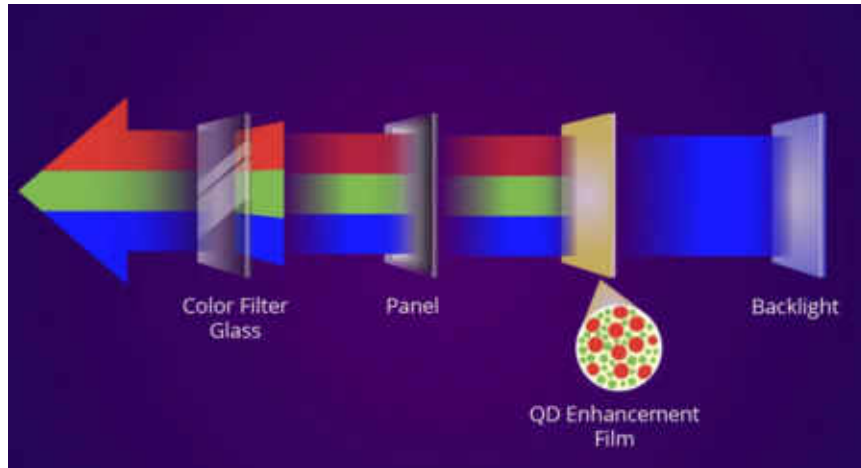


Color depends on the size of the QDs

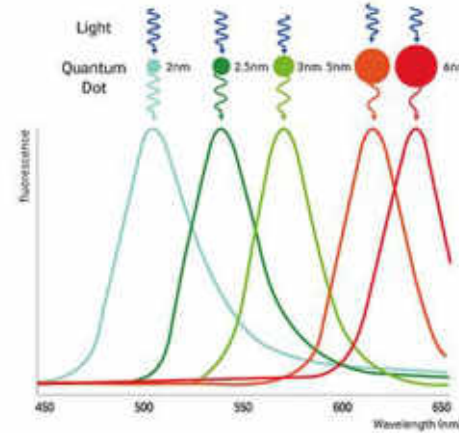

Energy efficient

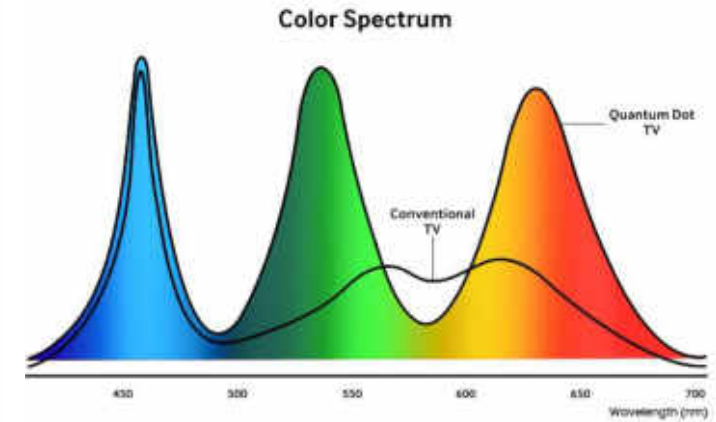


16 million colors

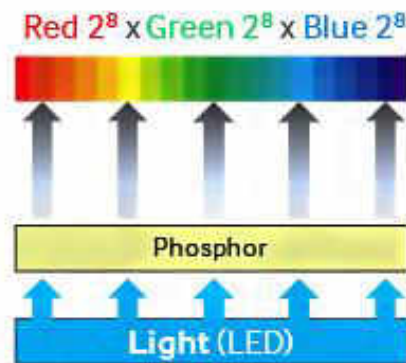

64x more color
than your average TV

Better light AND
energy efficiency

1 billion colors

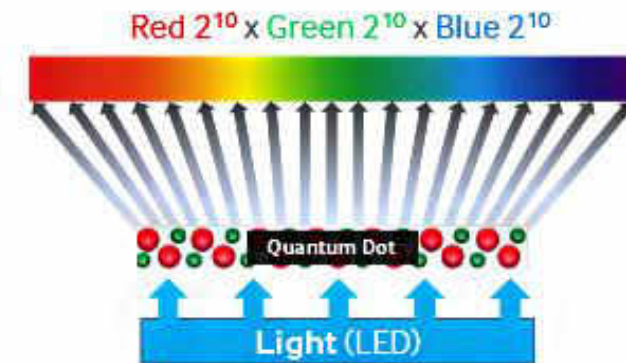

Capable of displaying wide color gamut



Discovery of quantum size effects

Part I : Quantum dots in glass matrix



Alexey I. Ekimov


Use of gold nanocrystals throughout the centuries

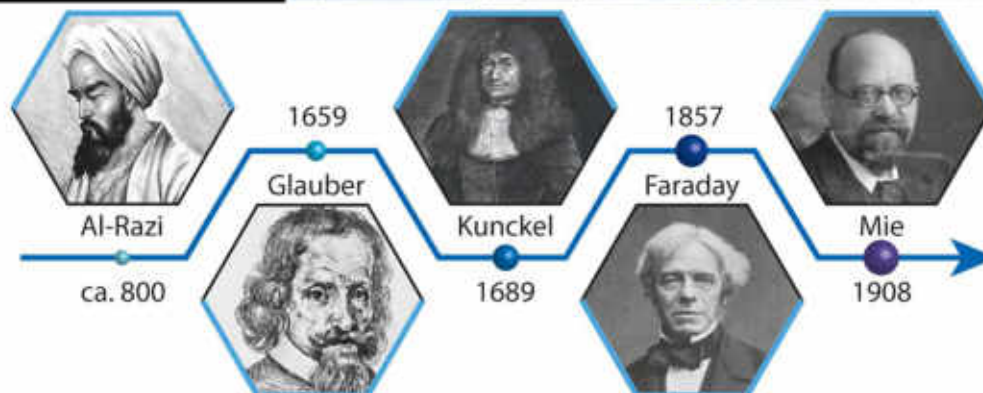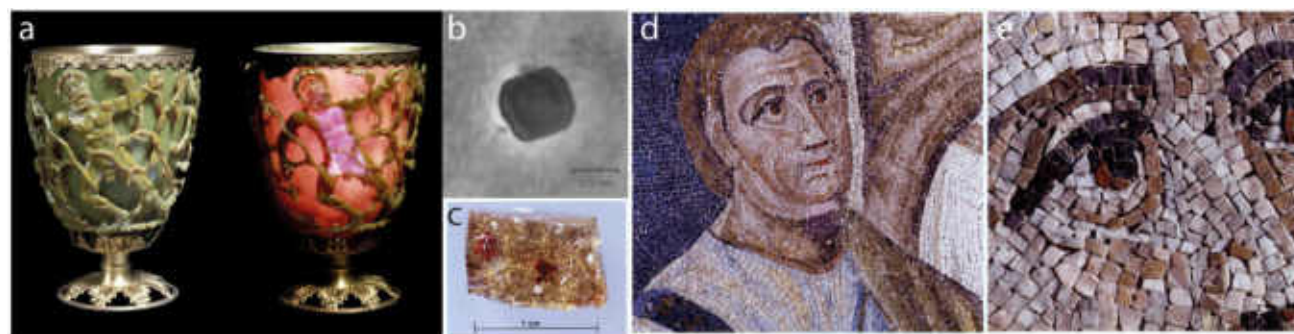

A—Furnace. B—In which water is put. C—In which the water is put. D—Mouth of the furnace. E—Chamber where the water is put. F—In which the water is put. G—In which the water is put. H—In which the water is put. I—In which the water is put. J—In which the water is put. K—In which the water is put. L—In which the water is put. M—In which the water is put. N—In which the water is put. O—In which the water is put. P—In which the water is put. Q—In which the water is put. R—In which the water is put. S—In which the water is put. T—In which the water is put. U—In which the water is put. V—In which the water is put. W—In which the water is put. X—In which the water is put. Y—In which the water is put. Z—In which the water is put.



Nanocrystals in glass throughout history

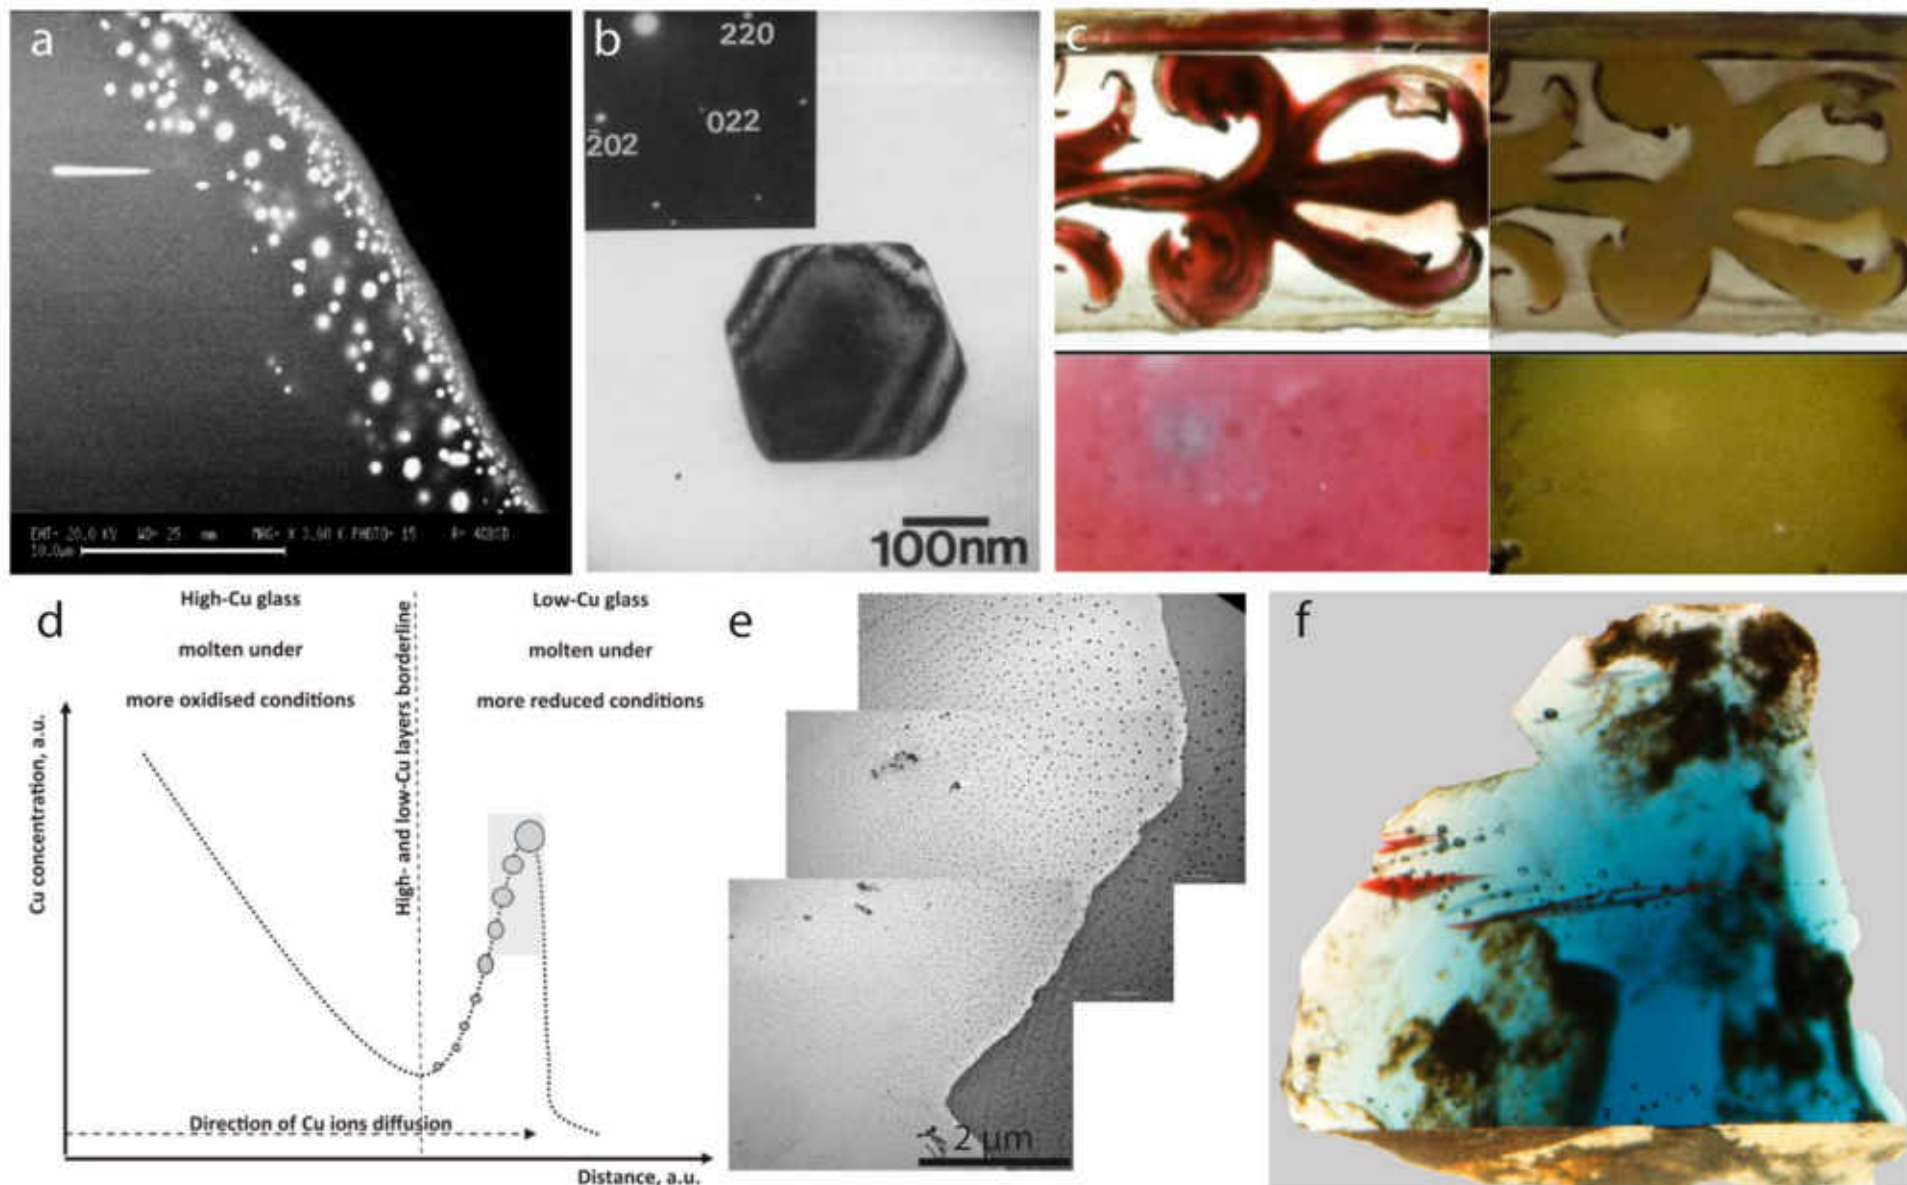

Quantum size effect in three-dimensional microscopic semiconductor crystals

A. I. Ekimov and A. A. Onushchenko

S. I. Vavilov State Optics Institute

(Submitted 29 July 1981)

Pis'ma Zh. Eksp. Teor. Fiz. **34**, No. 6, 363–366 (20 September 1981)


The exciton absorption spectrum of microscopic CuCl crystals grown in a transparent dielectric matrix has been studied. The size of the microscopic crystals was varied in a controlled manner from several tens of angstroms to hundreds of angstroms. There is a short-wave shift (of up to 0.1 eV) of the exciton absorption lines, caused by a quantum size effect.

PACS numbers: 61.60. + m, 71.35. + z


Size effects in semiconductors have recently attracted considerable interest. Most of the experiments which have been reported have used quasi-two-dimensional structures grown by molecular epitaxy,¹ MOS structures,² etc. In this letter we report the discovery and a spectroscopic study of a new class of objects that exhibit size effects: three-dimensional microscopic crystals of semiconducting compounds grown in a transparent dielectric matrix.

For the experiments we used multicomponent silicate glasses, with an initial composition including compounds of copper and chlorine at a concentration of the order of 1%. It was found recently³ that when such glasses are heated to a high temperature the characteristic exciton-absorption spectra of CuCl crystals appear in the


Observation of quantum size effects in microscopic CuCl crystals in Schott glasses

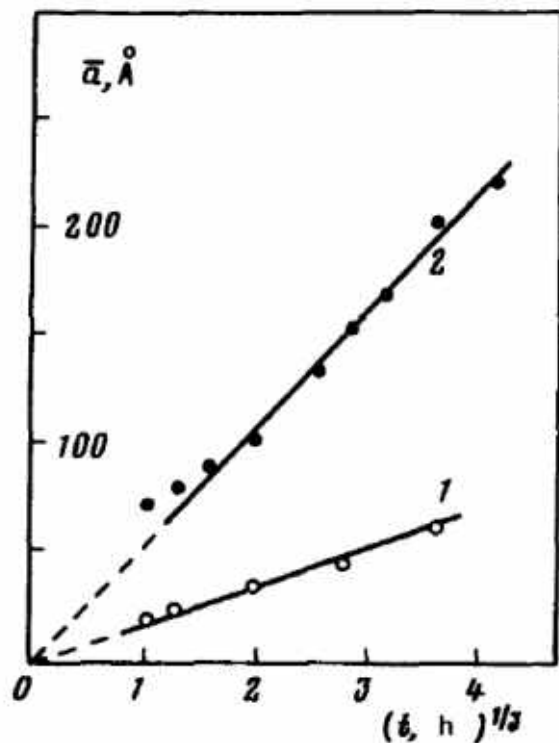

Dependence of the average radius of the CuCl crystals on the duration of heat treatment: 1 - 550°C; 2 - 625°C.

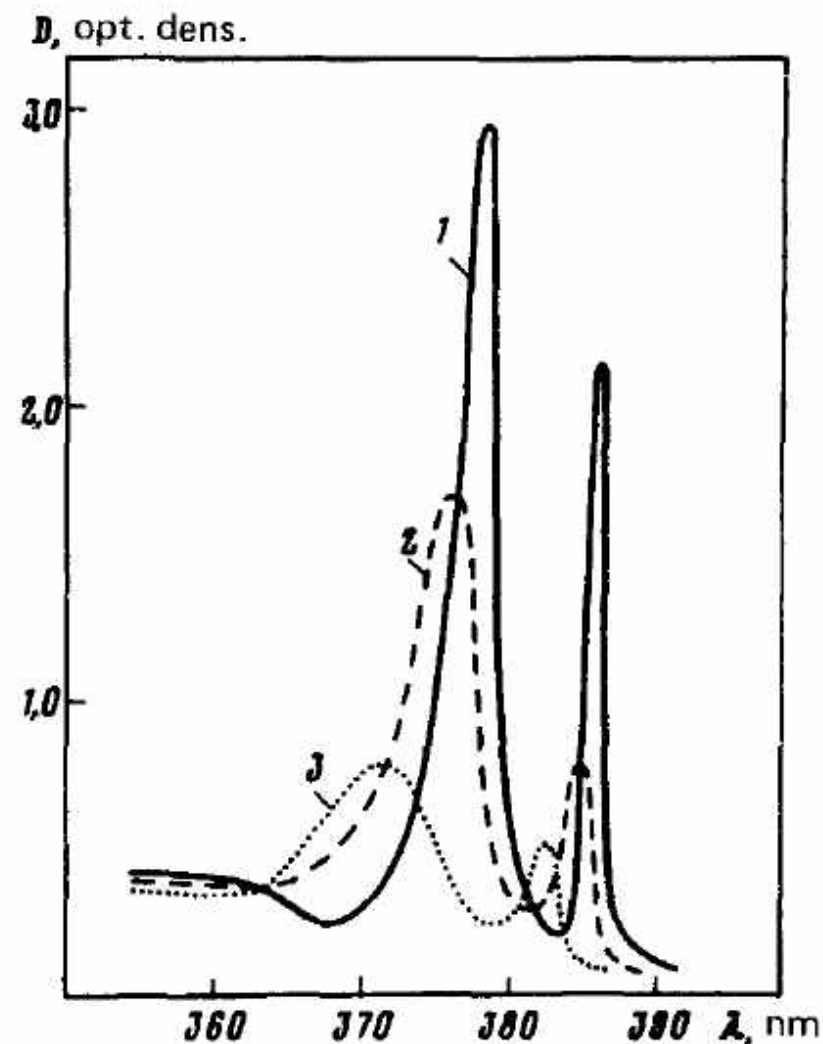

Absorption spectra of microscopic CuCl crystals at $T=4.2$ K with different average radii: 1 - 310 Å, 2 - 100 Å, c - 25 Å.

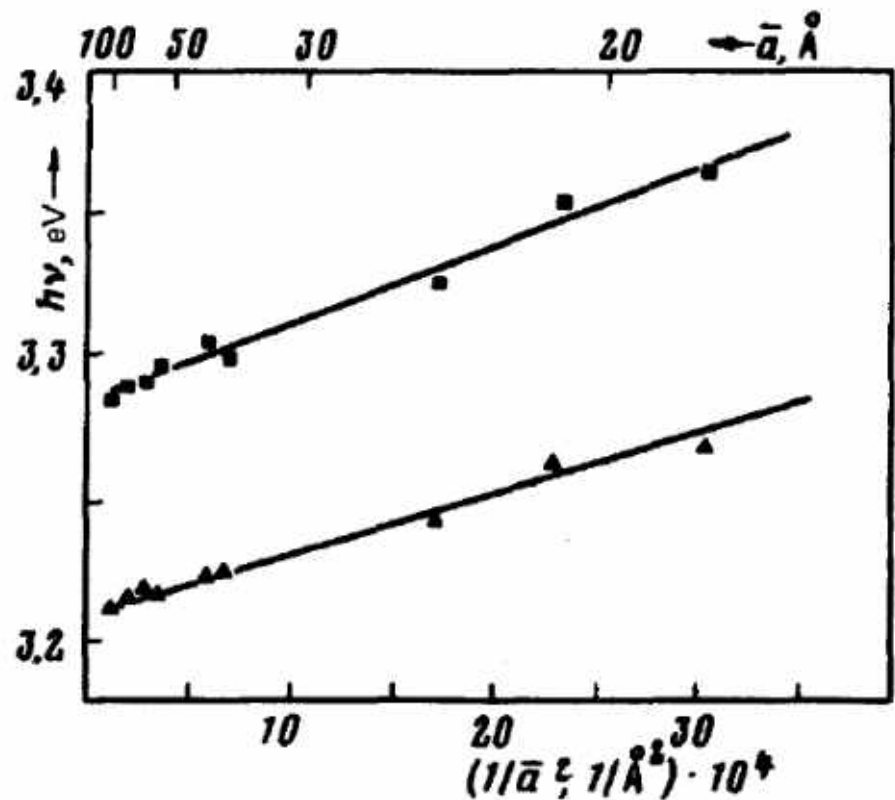

Photon energy $\hbar\omega$ of the exciton absorption line:

$$\hbar\omega = E_g - E_{ex} + \frac{\hbar^2\pi^2}{2M\bar{a}^2}$$

Here, E_g is the bulk material's semiconductor bandgap, E_{ex} is the exciton binding energy, and M is the charge carrier effective mass.

Dependence of the spectral positions of exciton absorption lines at $T = 4.2$ K on the average radius $\bar{a}$ of CuCl nanocrystals in glass. The energy of the absorption line increases proportional to $\bar{a}^{-2}$.

- Limitation of Ekimov's groundbreaking discovery was that his team's quantum dots were 'frozen' in glass and not suitable for further processing.

Discovery of quantum size effects

In colloidal quantum dots



Louis E. Brus

LETTERS TO THE EDITOR

The Letters to the Editor section is subdivided into four categories entitled Communications, Notes, Comments, and Errata. The textual material of each Letter is limited to 1200 words minus the following: (a) 200 words for a square figure (one column wide). Larger figures are scaled in proportion to their area; (b) 80 words for each displayed equation; (c) 7 words for each line of table including headings and horizontal rulings. Proof will be sent to authors. See the issue of 1 July 1983 for a fuller description of Letters to the Editor.

COMMUNICATIONS

Quantum size effects in the redox potentials, resonance Raman spectra, and electronic spectra of CdS crystallites in aqueous solution

R. Rossetti, S. Nakahara, and L. E. Brus

Bell Laboratories, Murray Hill, New Jersey 07974
(Received 31 March 1983; accepted 5 May 1983)

We report observation of size effects in the excited electronic properties of small, crystalline CdS particles. We also theoretically model the leading small size correction terms applicable to the photochemical redox potentials and lowest exciton energy. Our experiment involves controlled formation of CdS crystallites in aqueous solution; the photophysics and surface redox chemistry of electrons e^- and holes h^+ in these colloidal crystallites has been of recent interest.¹⁻⁴

Transmission electron microscope examination of particles from a freshly prepared colloid shows a narrow size distribution.⁵ A typical particle diameter is ≈ 35 Å, which corresponds to about six unit cells. The mass weighted average diameter $\bar{d}$ is ≈ 45 Å. The particles are crystalline (cubic CdS), with moderate diffraction ring broadening due to small crystallite size. In colloidal solution, thermodynamics favors growth of larger crystallites at the expense of smaller ones. We observe that, if these colloids "age" for ≈ 1 day at pH 3, the size distribution becomes broader with $\bar{d} \approx 125$ Å. On the average, 21 small crystallites dissolve and recrystallize onto one larger "seed" crystallite. The colloid remains transparent without CdS precipitation as it ages. The crystal structure is mixed cubic and hexagonal after aging; the hexagonal phase is thermodynamically more stable.

Resonance Raman (RR) spectroscopy⁶ in principle allows an *in situ* vibrational characterization despite the low crystallite concentration $\approx 2 \times 10^{-4}$ M in fresh colloids. The 416 nm RR spectrum in Fig. 1 shows the LO (longitudinal optical) phonon at 305 cm^{-1} and a weaker overtone near 605 cm^{-1} . These CdS peaks are superimposed on nearly continuous water Raman scattering. $e^- - h^+$ recombination luminescence has been largely quenched by addition of $\approx 10^{-5}$ M benzquinone.⁷ At 395, 448, and 460 nm similar spectra are observed. To the red (460, 503, and 532 nm) and to the blue (355 and 268 nm), the CdS RR spectra are far weaker and not detected.


To our knowledge these are the smallest isolated crystallites that have been examined by Raman spec-

troscopy.^{8,10} The LO peak occurs within a cm^{-1} of the bulk CdS frequency. In Fig. 1 the quency wing, in the region of expected surface maxima,¹¹ is slightly stronger than the high Γ wing. In other fresh colloids, the LO peak is asymmetrical. Shifts and surface mode maxima been reported for small crystalline grains in films.^{12,13}

In aged colloids the CdS RR excitation spectra changes markedly. RR scattering at 395, 441 nm is not detectable, with the cross section Γ mass decreasing by at least a factor of 10. There is no loss of CdS mass during aging; $\bar{d}$ from smaller to larger crystallites. CdS RR is detected in the red shifted and narrower range 460–480 nm. The spectra are similar Fig. 1, with an LO peak decrease of $\approx 3 \text{ cm}^{-1}$ slight narrowing.

The absorption spectrum also changes upon aging. As shown in the insert, absorption rises near and increases smoothly into the ultraviolet in aged colloids. The shape and absolute intensity of the are close to the extinction spectrum calculated Mie theory in the dipole limit,¹⁴ using the dielectric constants of bulk CdS.¹⁵ However, fresh colloid absorption edge blue shift of $\approx 0.2 \text{ eV}$, and appearance of a partially resolved feature at 44

The RR spectrum of bulk CdS is dominated phonon with an excitation spectrum peaking in region 460–480 nm, as in aged colloids.¹⁶⁻¹⁸ nanit intermediate state is the lowest (1B) Wannier, with a diameter of 55 Å and a binding energy 0.03 eV. In qualitative terms, quantum size effects should become important when crystallite size becomes commensurate with intrinsic exciton size. The aged colloids ($\bar{d} \approx 125$ Å) have RR and absorption behavior near to that observed for bulk material. In the fresh $\bar{d} \approx 45$ Å colloids, size effects occur in both RR and absorption spectra. The "exciton" (i.e., lowest excited state) is broadened and blue shifted.^{19,20} Quantum size effects in one dimension have been previously observed

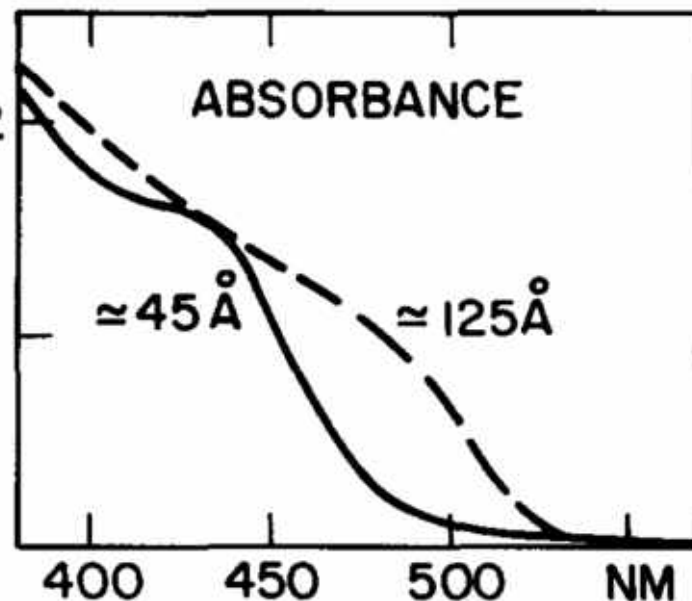

Size effects in the excited electronic states of small colloidal CdS crystallites

R. Rossetti, J. L. Ellison,^{*} J. M. Gibson, and L. E. Brus
Bell Laboratories, Murray Hill, New Jersey 07974

(Received 7 December 1983; accepted 25 January 1984)

This paper reports experimental studies of the development of bulk optical properties as a function of crystallite size for the inorganic direct gap semiconductor CdS. Small crystallites are synthesized via colloidal chemical techniques, and their optical properties are studied *in situ* at extreme dilution. The crystallites are characterized via high resolution transmission electron microscopy. Direct images show (111) lattice planes, and establish the crystallite structures as close to those of etched fragments of bulk CdS (zinc-blende cubic). Large crystallites (> 100 Å average diameter) show an optical absorption, in colloidal solution, close to that of bulk crystalline material. However, small crystallites of 30 Å average diameter show a large blue shift ($\approx 0.8 \text{ eV}$) in absorption edge (effective band gap), and an intensification of edge absorption relative to absorption at higher energy regions. These observations can be understood as quantum size effects resulting from confinement of an electron and hole in a small volume. 40 Å average size crystallites show a smaller shift ($\approx 0.25 \text{ eV}$), and corresponding changes in their fluorescence, and resonance Raman excitation, spectra.

INTRODUCTION

This experiment explores the development of bulk spectroscopic and electronic properties as a function of crystallite size for the semiconductor CdS. In general, semiconductors are materials in which the individual atomic components undergo strong intercomponent bonding. The properties of the bulk material are in nature and entirely different than those of the small molecules. We attempt to understand how these develop as a function of size, and whether intermediate size have properties that are not characteristic of either the atomic or bulk limits.

Our experimental approach to synthesis and characterization of small particles involves controlled reaction in a dilute extremely dilute colloidal crystallites, with immersion in the range 10^{-4} – 10^{-5} M. Chemical interest is in the catalytic properties of such colloidal and semiconductors.¹⁻⁴ Colloidal semiconductors utilized as photosensitizers, in that optical excitation of small particles creates an electron and hole which may individually react with adsorbed molecular species. This naturally arises as to the correct physical description of the confined electron and hole, i.e., as to the nature of the crystallite excited electronic states. This question depends intimately upon the actual structure of the aggregate. In this paper we characterize colloidal crystallites with high-resolution transmission microscopy (TEM), and correlate changes in dimensions changes in the electronic absorption, resonance and fluorescence spectra.

The solubility product of CdS in water is so low that, if a dilute Cd^{2+} solution is mixed with S^{2-} solution at higher concentration, Cd^{2+} will exist almost entirely in the form of solid CdS when equilibrium is achieved. The size of the initial crystallites formed is controlled by kinetic considerations during mixing. Their stability, once

^{*} Bell Laboratories undergraduate research student.

formed, is influenced by the dynamic equilibrium

$$[\text{CdS}]_{\text{crystallite}} = [\text{Cd}^{2+}]_{\text{free}} + [\text{S}^{2-}]_{\text{free}} \quad (1)$$

This equilibrium is a function of both crystallite size and solvent dielectric constant. Small crystallites are less stable than large crystallites and tend to dissolve rapidly.⁵ The dissolved ions can recrystallize on larger crystallites where thermodynamic stability is higher. The net effect is that mass transfers from smaller to larger crystallites as a function of time—an effect long known as "aging" or Ostwald ripening. In principle, such aging can be reduced, and thus the lifetime of small crystallites enhanced, in a solvent of low dielectric constant where dissolved ions are less stable than in water. The equilibrium is shifted to the left hand side in Eq. (1). We study an aqueous CdS colloid in both its initial and aged form. We also study a CdS colloid in acetonitrile, a solvent of lower dielectric constant ($\epsilon \approx 36$), in which smaller crystallites are obtained.


In this manuscript we first establish experimentally that the colloidal particles are crystalline, and that the optical properties are a function of size. To our knowledge, this work (along with our earlier Communication⁶) is the first report of a correlation between semiconductor crystallite size and optical properties. We then compare these observations with the predictions of the elementary model of an electron and hole confined in a small crystallite.⁹

II. EXPERIMENTAL

Both acetonitrile and aqueous colloids contain 0.1% by weight of styrene/maleic anhydride copolymer, a stabilizing agent used to prevent coagulation and flocculation. While the role of the copolymer is not fully understood, the dissolved copolymer has negative carboxylate groups which apparently complex with Cd^{2+} surface ions on the CdS crystallites.

The aqueous colloid was prepared by slowly injecting with a syringe 20 cc of 9.3×10^{-3} M CdSO_4 solution into 100 cc of a stirring $\approx 5 \times 10^{-3}$ M $(\text{NH}_4)_2\text{S}$ solution (containing


Evidence of quantum size effects in colloidal nanoparticles

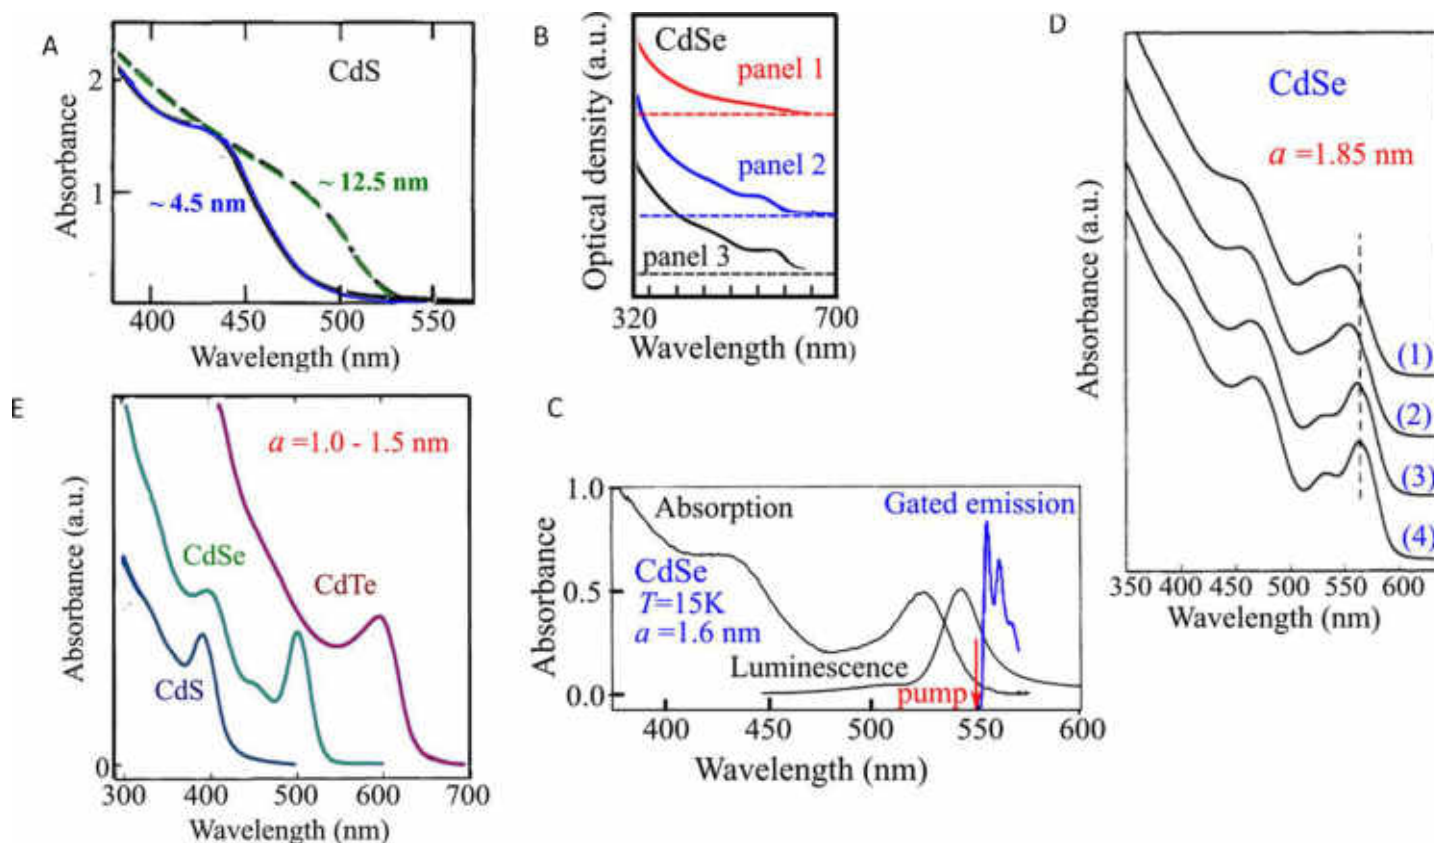

Nucleation and growth of NCs in an aqueous solution. (A) Room-temperature absorption spectra of “fresh” and aged for 1 day CdS NC in aqueous solution. (B) Room-temperature absorption spectra of CdSe NC grown by inverse micelle approach, before (panel 1) and after (panel 2) postreaction annealing as well as wurtzite CdSe NCs resulting from high-temperature refluxing (panel 3). (C) Photoluminescence from 1.6 nm radius CdSe NC and its resonance photoexcitation. (D) Sharpening of CdSe NC absorption spectra introduced by size-selective precipitation. (E) Absorption spectra of CdS, CdSe, and CdTe NCs.

Rossetti, R.; Nakahara, S.; Brus, L. E. J Chem Phys 1983, 79 (2), 1086-1088.
 Rossetti, R.; Ellison, J. L.; Gibson, J. M.; Brus, L. E. Chem Phys 1984, 80 (9), 4464-4469.
 Brus, L. E. J Chem Phys 1983, 79 (11), 5566-5571.
 Steigerwald, M. L.; Brus, L. E. Acc. Chem. Res. 1990, 23, 183-188.

Theoretical ideas from 1980s

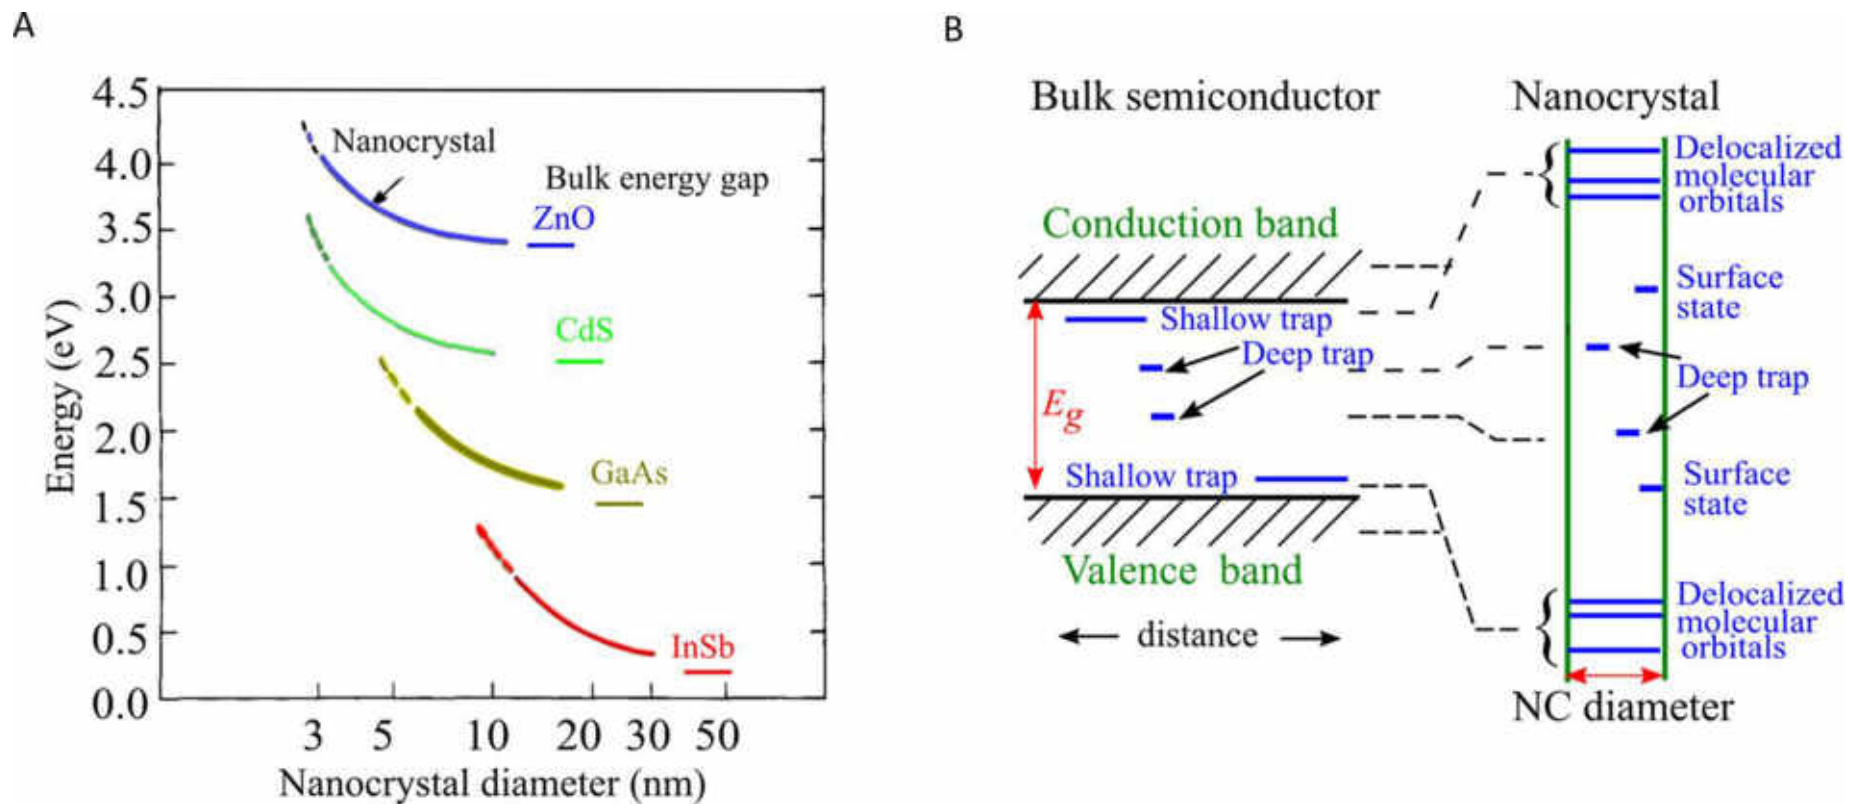

(A) Calculated size-dependent shift of the lowest exciton levels in strong confinement. (B) Spatial electronic state correlation diagram for bulk semiconductors and NCs.

Brus, L. E. J Chem Phys 1984, 80 (9), 4403-4409.
 Brus, L. E. J Phys Chem 1986, 90 (12), 2555-2560.

- The discovery of quantum size effects in colloidal nanocrystals stimulated significant research efforts in understanding their optical and photochemical properties, in the hope of being able to use size to design desirable physical and chemical properties.
- Limited homogeneity and quality of the available nanocrystals, with variations in size, shape, crystallinity and surface electronic defects made it difficult to isolate inherently size-dependent behaviour. For example, luminescence from nanocrystals available in the late 1980s was typically limited by a quantum yield of only a few percent.

Synthesis

Improved universal synthetic methodology



Moungi G. Bawendi

Synthesis and Characterization of Nearly Monodisperse CdE (E = S, Se, Te) Semiconductor Nanocrystallites

C. B. Murray, D. J. Norris, and M. G. Bawendi*

Contribution from the Department of Chemistry, Massachusetts Institute of Technology, Cambridge, Massachusetts 02139

Received March 22, 1993

Abstract: A simple route to the production of high-quality CdE (E = S, Se, Te) semiconductor nanocrystallites is presented. Crystallites from ~ 12 Å to ~ 115 Å in diameter with consistent crystal structure, surface derivatization, and a high degree of monodispersity are prepared in a single reaction. The synthesis is based on the pyrolysis of organometallic reagents by injection into a hot coordinating solvent. This provides temporally discrete nucleation and permits controlled growth of macroscopic quantities of nanocrystallites. Size selective precipitation of crystallites from portions of the growth solution isolates samples with narrow size distributions ($<5\%$ rms in diameter). High sample quality results in sharp absorption features and strong "band-edge" emission which is tunable with particle size and choice of material. Transmission electron microscopy and X-ray powder diffraction in combination with computer simulations indicate the presence of bulk structural properties in crystallites as small as 20 Å in diameter.

1. Introduction

The study of nanometer sized crystallites provides an opportunity to observe the evolution of material properties with size. This intermediate size regime is where the collective behavior of bulk materials emerges from the discrete nature of molecular properties. The differing rates with which each of the bulk properties develops provides the possibility of observing and perhaps controlling novel behavior. Nonlinear optical effects from highly polarizable excited states and novel photochemical behavior are two such examples.¹

The physical properties of semiconductor nanocrystallites are dominated by the spatial confinement of excitations (electronic and vibrational). Quantum confinement, the widening HOMO-LUMO gap with decreasing crystallite size, and its implications for the electronic structure and photophysics of the crystallites have generated considerable interest.^{1,2} A number of optical studies have begun probing the photoexcited states in such crystallites.^{1,3}

Although considerable progress has been made in the controlled synthesis of II-VI semiconductor crystallites,^{1,3} interpretation of sophisticated optical experiments often remains difficult due to

polydispersities in size and shape, surface electronic defects due to uneven surface derivatization, and poor crystallinity. The study of an appropriate high quality model system is essential in distinguishing properties truly inherent to the nanometer size regime from those associated with variations in sample quality. Each sample must display a high degree of monodispersity (size, shape, etc.), regularity in crystallite core structure, and a consistent surface derivatization (cap).

This paper presents a relatively simple synthetic route to the production of high-quality nearly monodisperse ($<5\%$ rms in diameter) samples of CdE (E = S, Se, Te) nanometer size crystallites, with the emphasis on CdSe. The synthesis begins with the rapid injection of organometallic reagents into a hot coordinating solvent to produce a temporally discrete homogeneous nucleation. Slow growth and annealing in the coordinating solvent results in uniform surface derivatization and regularity in core structure. Size selective precipitation provides powders of nearly monodisperse nanocrystallites which can be dispersed in a variety of solvents. The crystallites are slightly prolate with an aspect ratio of 1.1 to 1.3. The average crystallite size, defined by its major axis, is tunable from ~ 12 to ~ 115 Å. Room temperature optical absorption and luminescence experiments show that the samples are of high optical quality. Transmission electron microscopy and X-ray powder diffraction are used in combination with computer simulations to characterize nanocrystallite structural features.

II. Experimental Section

General. All manipulations involving alkylcadmium, silylchalcogenides, phosphines, and phosphine chalcogenides were carried out using standard airless procedures. Tri-*n*-octylphosphine (TOP) and bis(trimethylsilyl)sulfide [(TMS)₂S] were used as purchased from Fluka. Electronic grade (99.99+%) selenium and tellurium shot were purchased from Alfa. Anhydrous methanol, 1-butanol, pyridine, and hexane were purchased from a variety of sources. Tri-*n*-octylphosphine oxide [TOPO] was purchased from Alfa and purified by distillation, retaining the fraction transferred between 260 and 300 °C at ~ 1 Torr. Dimethylcadmium [Me₂Cd] was purchased from Organometallics Inc. and purified by filtration (0.250 μm) and vacuum transfer. Bis(trimethylsilyl)selenium [(TMS)₂Se] and bis(trimethylsilyl)tellurium [(TMS)₂Te] were prepared via literature methods³⁴ and stored at -35 °C in a drybox. Appropriate masses of selenium and tellurium shot were dissolved directly

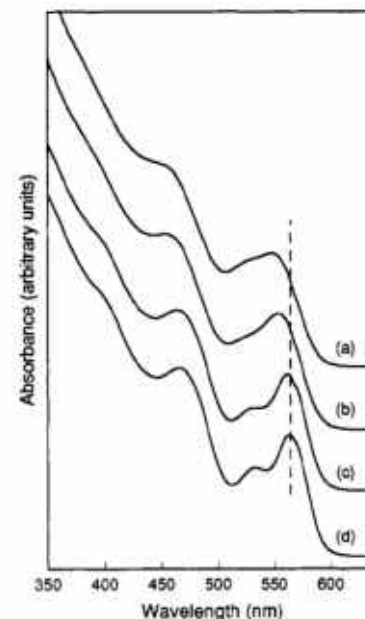


Figure 1. Example of the effect of size-selective precipitation on the absorption spectrum of ~ 37 Å diameter CdSe nanocrystallites. (a) Room temperature optical absorption spectrum of the nanocrystallites in the growth solution before size-selective precipitation. (b) Spectrum after one size-selective precipitation from the growth solution with methanol. (c) Spectrum after dispersion in 1-butanol and size-selective precipitation with methanol. (d) Spectrum after a final size-selective precipitation from 1-butanol/methanol.

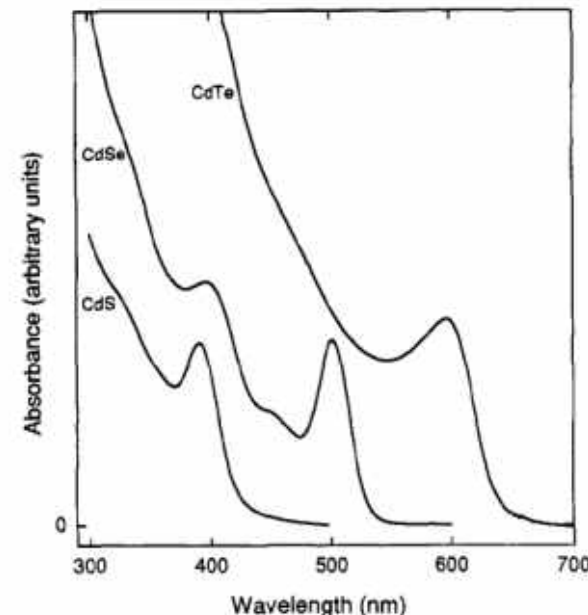


Figure 2. Room temperature optical absorption spectra of ~ 20 – 30 Å diameter CdS, CdSe, and CdTe crystallites.


(1) Recent reviews include: (a) Brus, L. E. *Appl. Phys. A* **1991**, *53*, 465. (b) Henglein, A. *Top. Curr. Chem.* **1988**, *143*, 113. (c) Wang, Y.; Herron, N. J. *Phys. Chem.* **1991**, *95*, 525. (d) Bawendi, M. G.; Steigerwald, M. L.; Brus, L. E. *Annu. Rev. Phys. Chem.* **1990**, *41*, 477. (2) Recent optical studies include the following: (a) Rossignol, P.; Ricard, D.; Flytzanis, C.; Neuzil, N. *Phys. Rev. Lett.* **1989**, *62*, 312. (b) Alivisatos, A. P.; Harris, A.; Levins, N.; Steigerwald, M.; Brus, L. E. *J. Chem. Phys.* **1989**, *89*, 4001. (c) Peyghambarian, N.; Fliegel, B.; Hulin, D.; Migus, A.; Joffe, M.; Antonetti, A.; Koch, S. W.; Lindberg, M. *IEEE J. Quantum Electron.* **1989**, *25*, 2516. (d) Bawendi, M. G.; Wilson, W. L.; Rothberg, L.; Carroll, P. J.; Jais, T. M.; Steigerwald, M. L.; Brus, L. E. *Phys. Rev. Lett.* **1990**, *65*, 1623. (e) Bawendi, M. G.; Carroll, P. J.; Wilson, W. L.; Brus, L. E. *J. Chem. Phys.* **1992**, *96*, 946. (f) Alivisatos, A. P.; Harris, T. D.; Carroll, P. J.; Steigerwald, M. L.; Brus, L. E. *J. Chem. Phys.* **1989**, *90*, 3403. (g) O'Neil, M.; Macdon, J.; McLendon, G. *J. Phys. Chem.* **1990**, *94*, 4356. (h) Eychmüller, A.; Hasserlberth, A.; Katsikas, L.; Weller, H. *Ber. Bunsenges. Phys. Chem.* **1991**, *95*, 79. (i) Wang, Y.; Suna, A.; McHugh, J.; Hillinski, E.; Lucas, P.; Johnson, R. D. *J. Chem. Phys.* **1990**, *92*, 6927. (j) Eck, V.; Fliegel, B.; Chitron, G.; Gibbs, M.; Fajila, S.; Chang, S. W.; Koch, S. W.; Liu, L. C.; Rabaud, S. W.; Peyghambarian, N. *Phys. Rev. B* **1990**, *42*, 7450. (k) Ekimov, A. I.; Hache, F.; Schanne-Klein, M. C.; Ricard, D.; Flytzanis, C.; Kudryavtsev, I. A.; Yazeva, T. V.; Rodina, A. F.; Elron, A. L. *J. Opt. Soc. Am. B* **1993**, *10*, 100. (3) (a) Steigerwald, M. L.; Alivisatos, A. P.; Gibson, J. M.; Harris, T. D.; Kortan, R.; Muller, A. J.; Thayer, A. M.; Donlan, T. M.; Donaghy, D. C.; Brus, L. E. *J. Am. Chem. Soc.* **1987**, *109*, 1040. (b) Breneman, J. G.; Siegrist, T.; Carroll, P. J.; Stuczynski, S. M.; Brus, L. E.; Steigerwald, M. L. *J. Am. Chem. Soc.* **1989**, *111*, 4141. (c) Spatzel, L.; Haase, M.; Weller, H.; Henglein, A. *J. Am. Chem. Soc.* **1987**, *109*, 5649.

(4) Dery, M. R.; Seidler, M. D. *J. Org. Chem.* **1982**, *47*, 1354.


The hot-injection synthesis

How Moungi Bawendi produced quantum dots


- 1 Bawendi injected substances that can form cadmium selenide into hot solvent. The volume was enough to saturate the solvent around the needle.

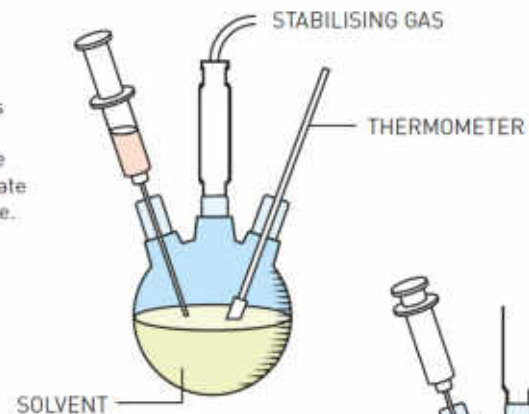


- 2 Small crystals of cadmium selenide immediately formed, but because the injection cooled the solvent the crystals stopped forming.

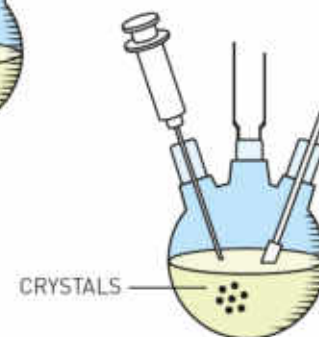


- 3 When Bawendi increased the temperature of the solvent, the crystals once again started to grow. The longer this continued, the larger the crystals became.

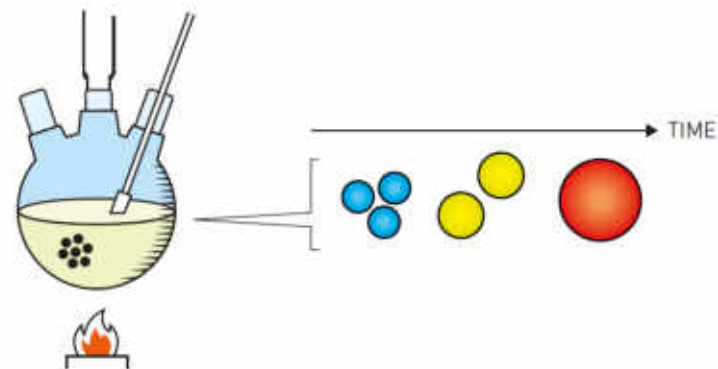

Synthesis and Characterization of Nearly Monodisperse Cde (E = S, Se, Te) Semiconductor Nanocrystallites

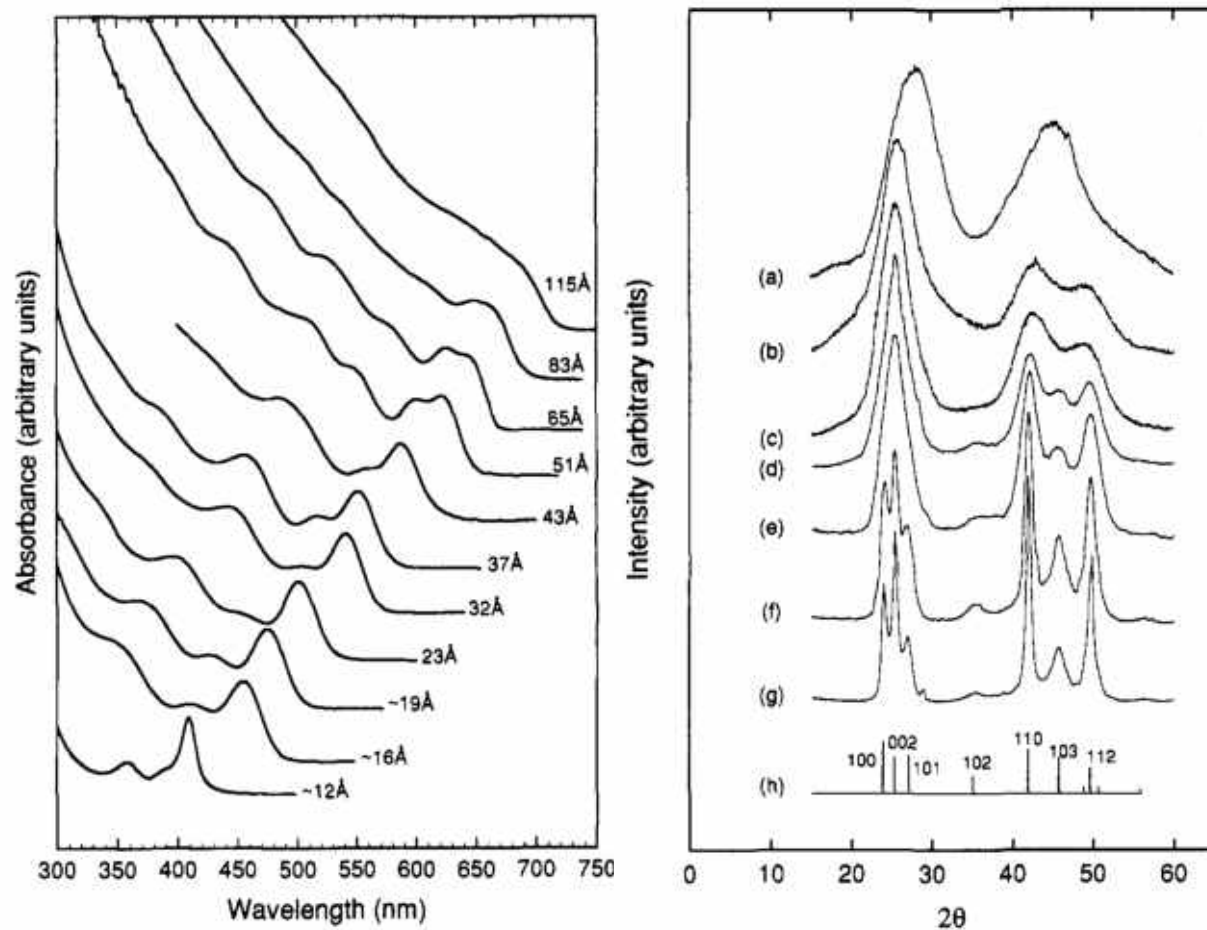

UV-visible spectrum and corresponding XRD pattern of CdS nanocrystals

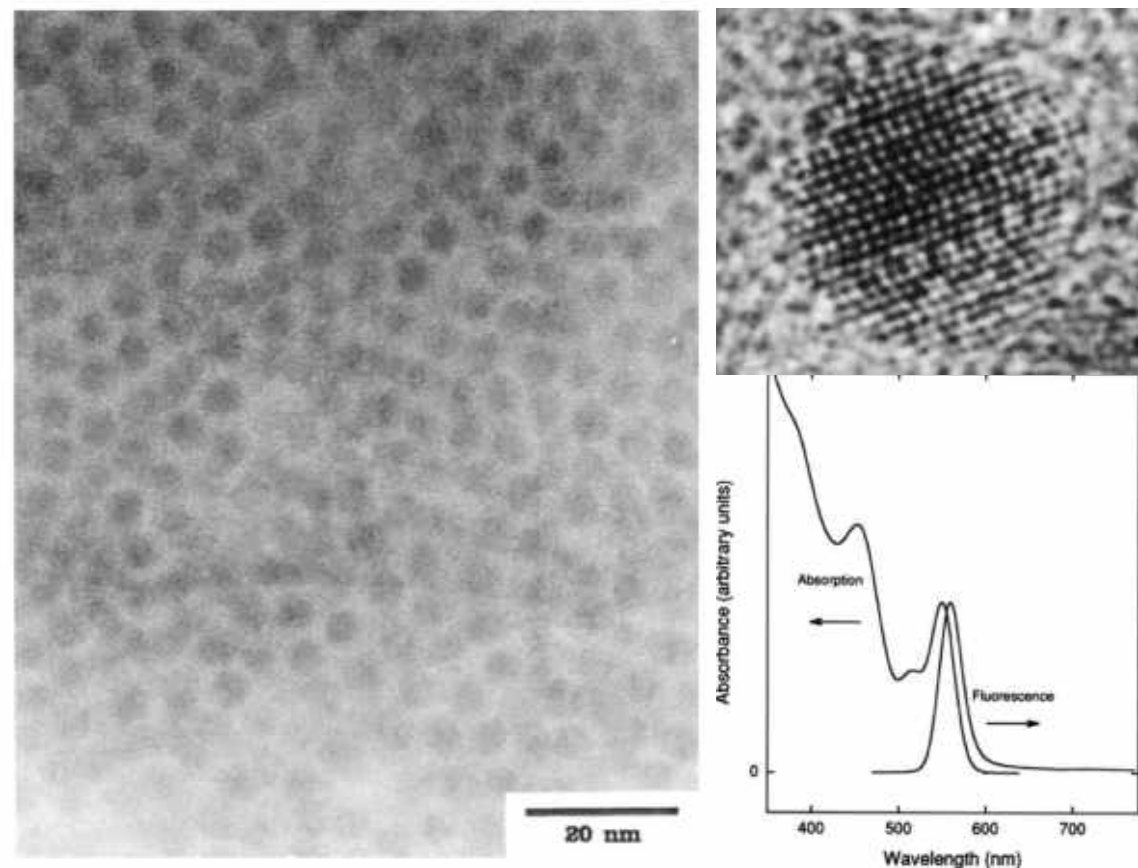


TEM and HRTEM image of CdSe nanocrystal with an average diameter of 5.1 nm. Luminescent spectrum of 3.5 nm CdSe nanocrystals.

Technological milestones

Quantum dots: Seeds of Nanoscience

Light-emitting diode (LED) from CdSe nanocrystals and a semiconducting polymer

- Light emission arises from the recombination of holes injected into a layer of semiconducting p-paraphenylene vinylene (PPV) with electrons injected into a multilayer film of cadmium selenide nanocrystals.
- Close matching of the emitting layer of nanocrystals with the work function of the metal contact leads to an operating voltage of only 4V.
- Due the quantum size effect the colour of this emission can be varied from red to yellow by changing the nanocrystal size.

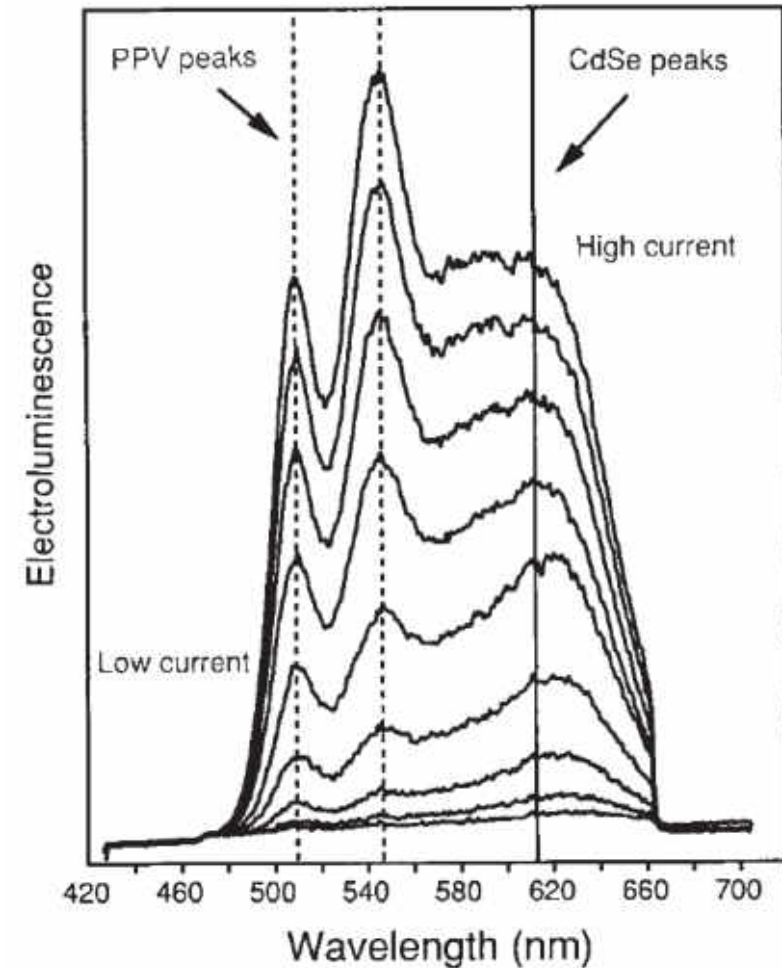


Colvin, V. L.; Schlamp, M. C.; Alivisatos, A. P. *Nature* 1994, 370 (6488), 354-357.


Voltage dependent color of CdSe/PPV (p-paraphenylene vinylene) samples.

Core-shell quantum dots

- Core-shell nanoparticles were created that consisted of a wide-bandgap shell, such as ZnS, to confine electrons and holes to a small-bandgap core (such as CdSe).
- In this way, the charge carriers in the core were separated from surface states, such as unsaturated bonds, that are detrimental to optical performance.
- The resulting CdSe/ZnS core-shell quantum dots had a luminescence quantum yield at room temperature of up to 50%, with better long-term stability and reduced bleaching.

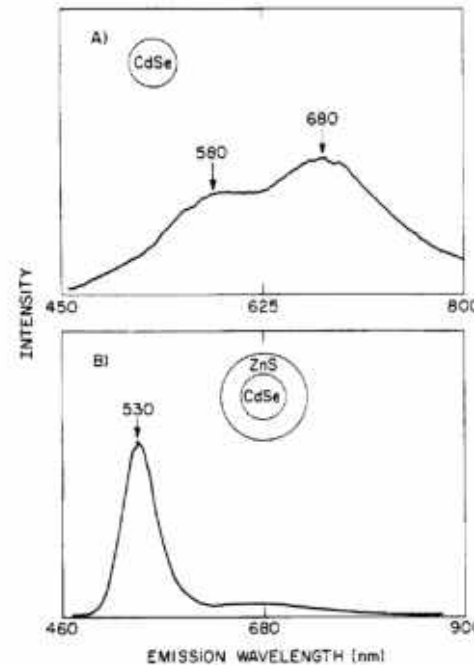

Room temperature luminescence spectra: (A) CdSe, (B) (CdSe)ZnS. The integrated quantum yield in B is more than an order of magnitude higher than in A.

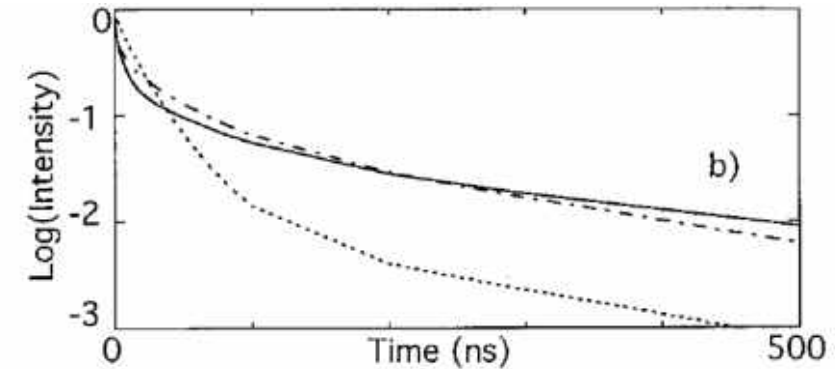


Reconstructed time decay plot: (CdSe)ZnS – solid line, (CdSe)TOPO – dashed line.

Melting in semiconductor nanocrystals

Temperature-dependent electron diffraction studies on nanocrystals of CdS show a large depression in the melting temperature with decreasing size, as a larger fraction of the total number of atoms is on the surface.


Implications:

- The optimum annealing temperature for preparation of high-quality defect-free nanocrystals can be expected to be a small fraction of the bulk annealing temperature.
- The ability to fuse nanocrystals to form a film at relatively modest temperatures indicates that nanocrystals may provide a new low-temperature route to thin-film growth.

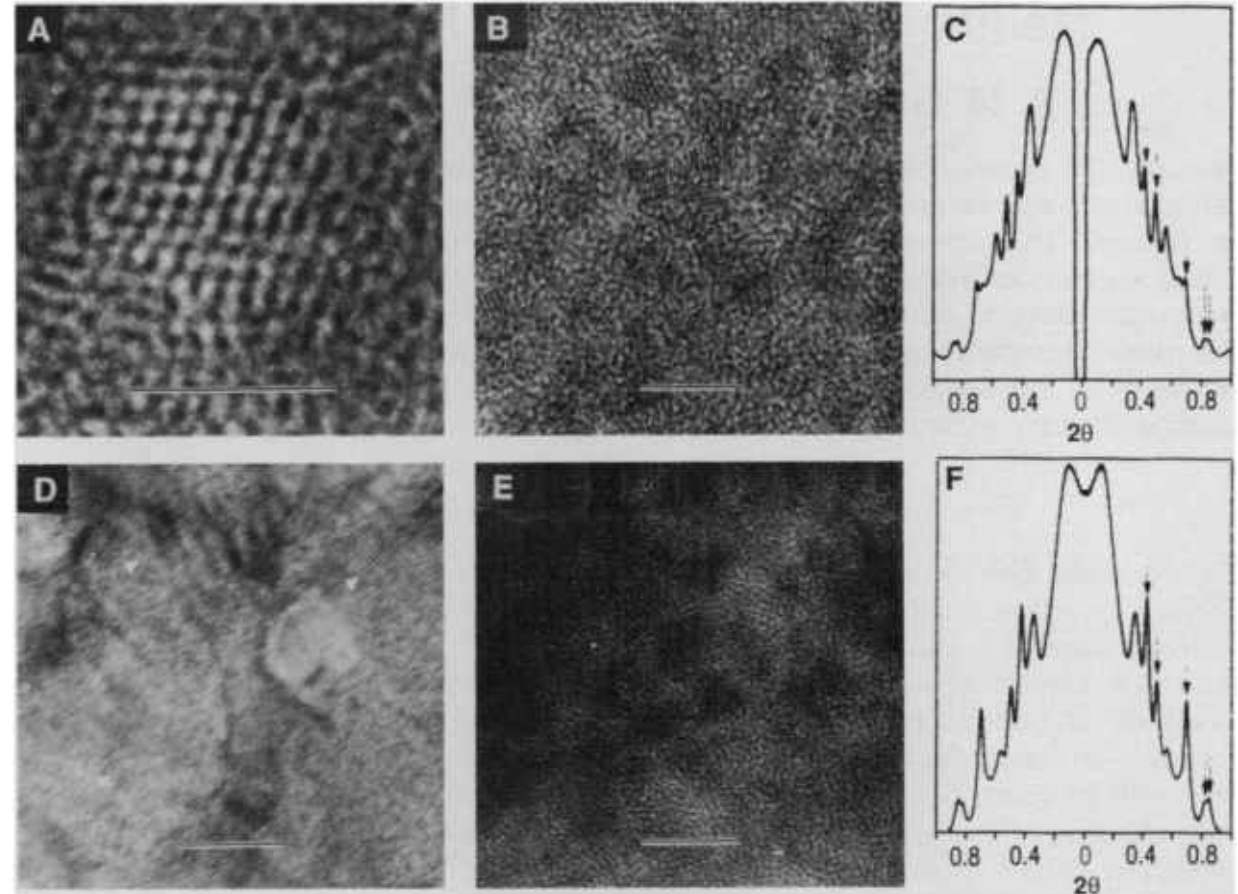



Synthesis of water-soluble quantum dots - new tool for labelling biomolecules

Functionalization using polysilanes

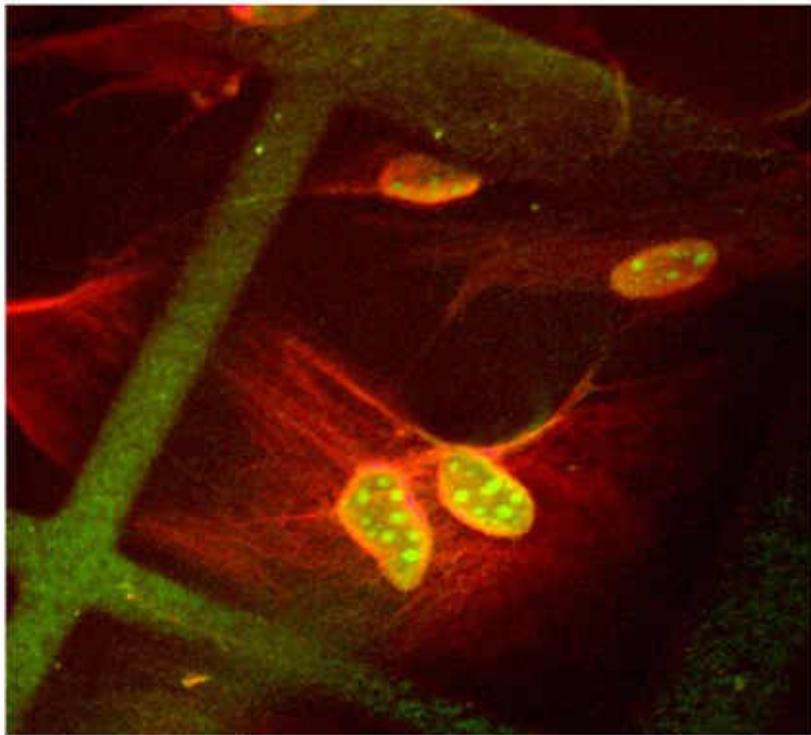


Two-color labeling of mouse 3T3 fibroblast with green and red CdSe NCs.

Functionalization using thiols

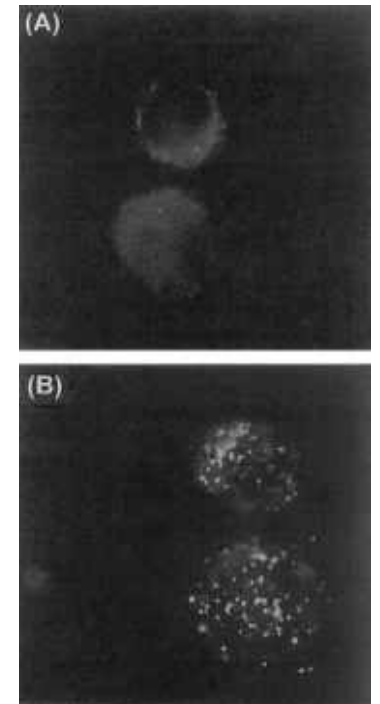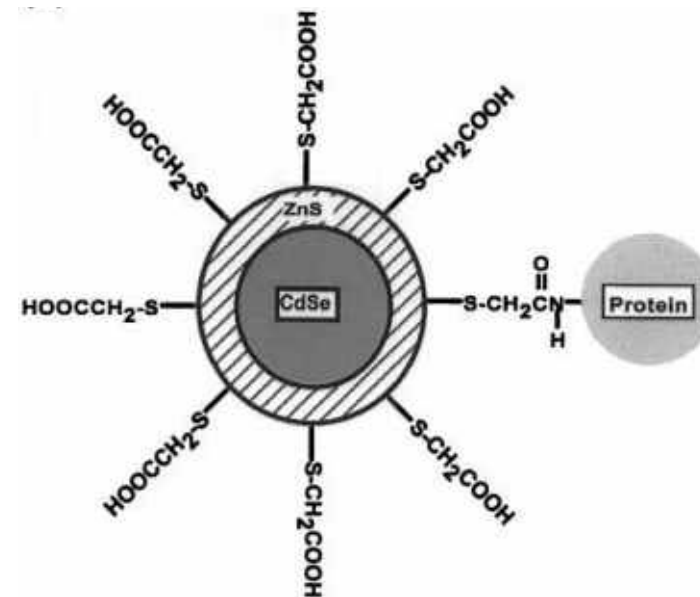


Left: Schematic of a ZnS-capped CdSe QD that is covalently coupled to a protein by mercaptoacetic acid. Right: Luminescence images of cultured HeLa cells that were incubated with (A) mercapto-QDs and (B) QD-transferrin conjugates.

Shape control of nanocrystals - nanorods


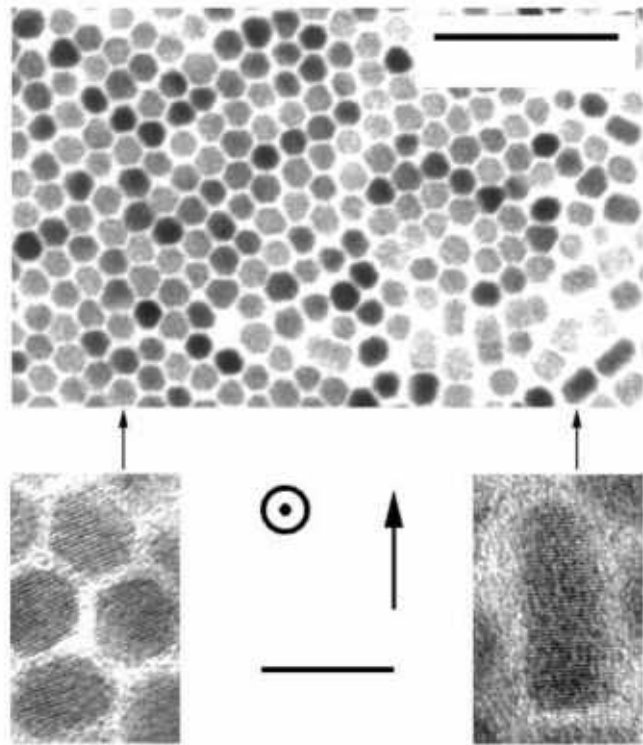


Three-dimensional orientation of CdSe quantum rods observed by TEM.

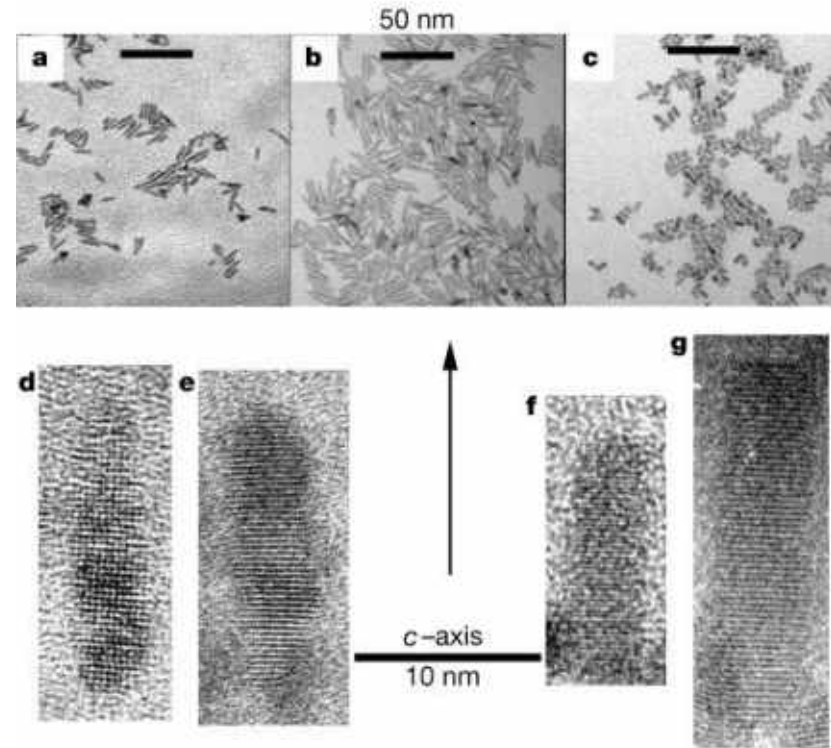

TEM images of different samples of quantum rods. A-c, Low-resolution TEM images of three quantum-rod samples with different sizes and aspect ratios. d-g, High resolution TEM images of four representative quantum rods. d and e are from the sample shown in a; f and g are from the sample shown in c.


Shape control of nanocrystals – branched rods

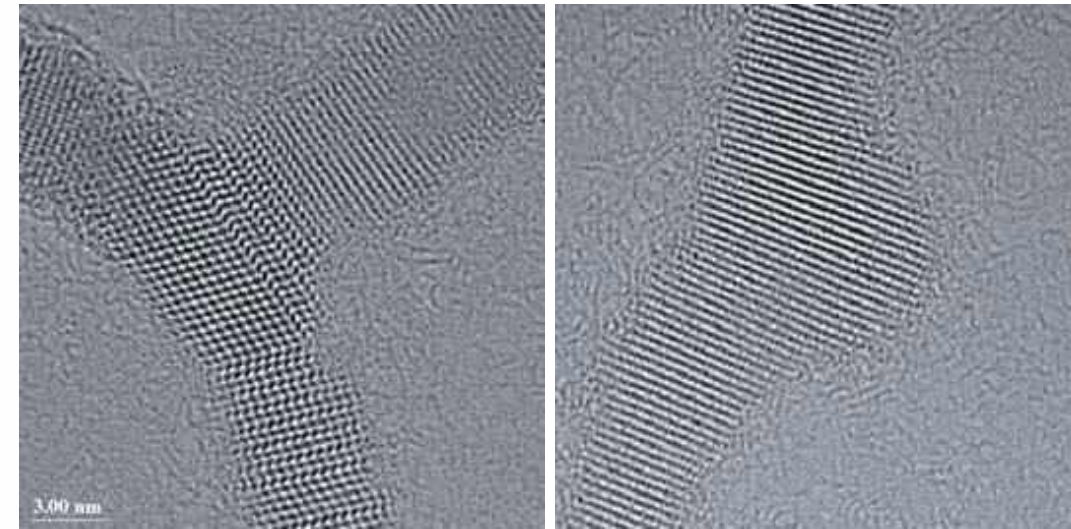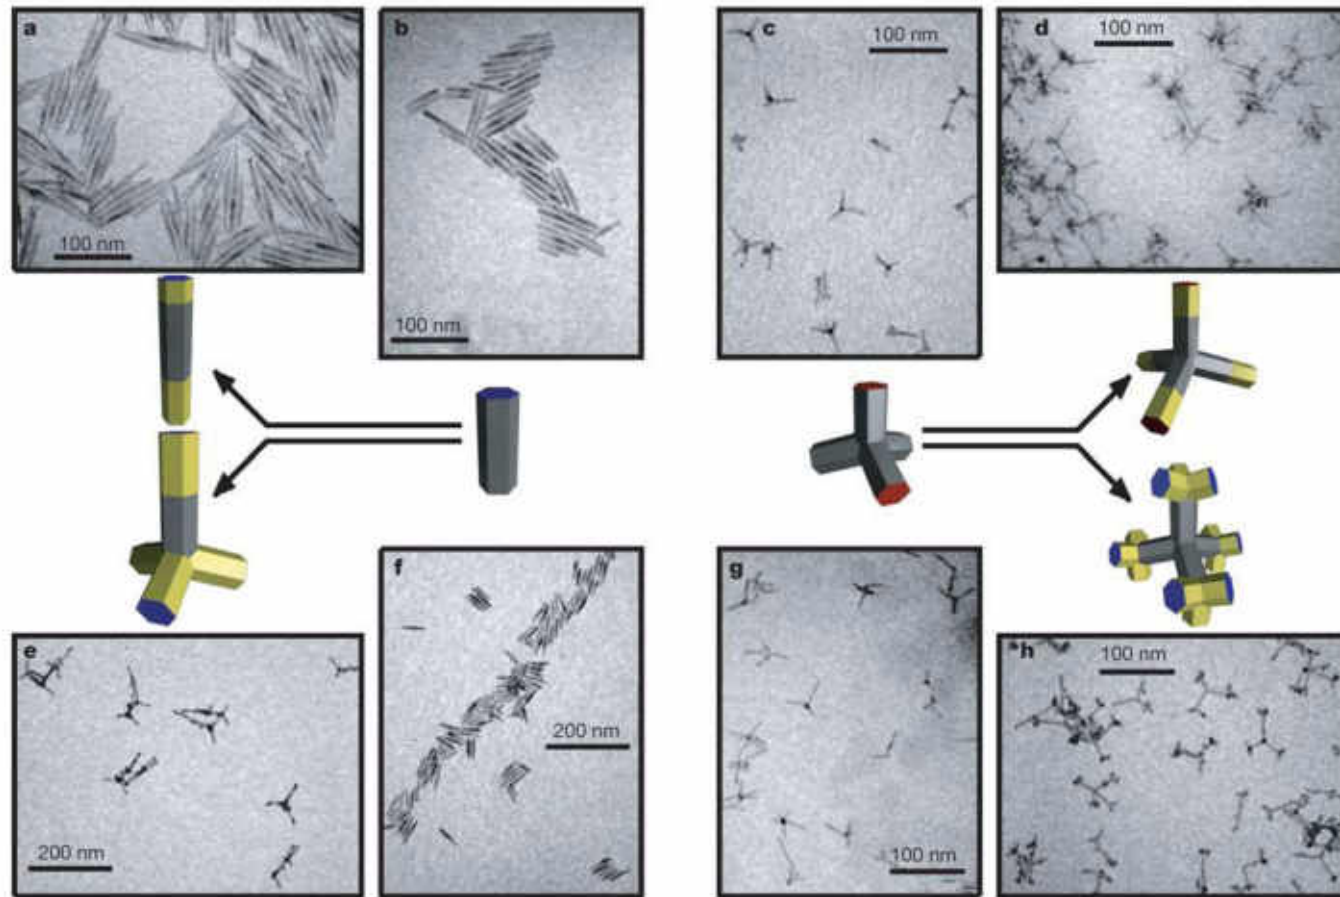

High-resolution electron microscopy of heterojunctions. a, HRTEM of a branch point shows a zincblende core and wurtzite branches of CdTe and an original wurtzite rod (upper right) of CdSe. b, Examination of a linear junction between CdSe (upper right) and CdTe reveals continuous wurtzite growth.

Cation exchange reaction


Before
Exchange: CdSe

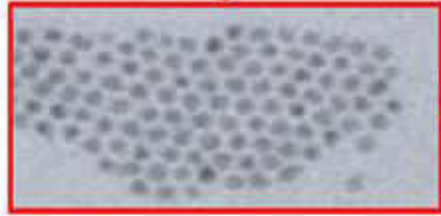


After
Exchange: Ag₂Se



Reverse
Exchange: CdSe

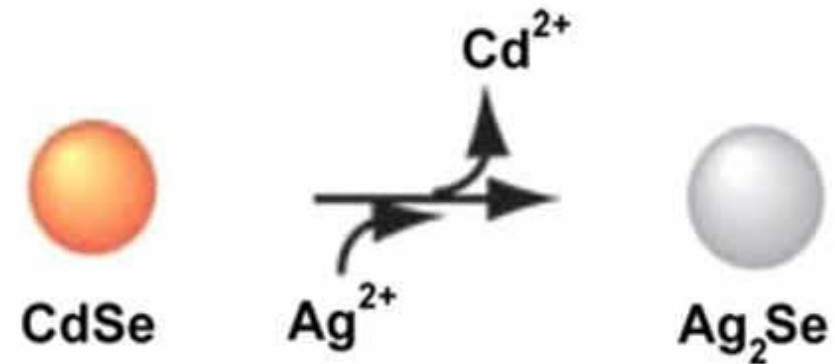


X-ray
Diffraction

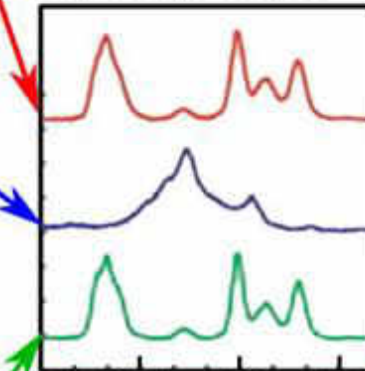


20 35 50 65
Diffraction
Angle

Fluorescence

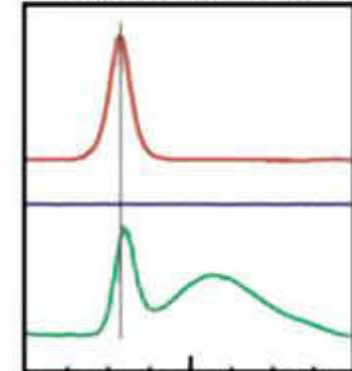


450 650 850

Absorption

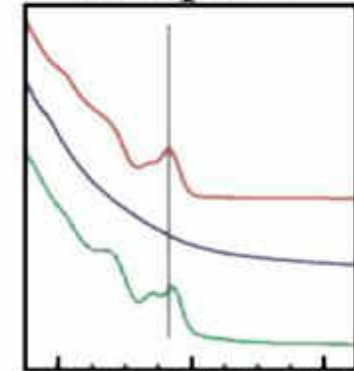


400 600 800
Wavelength (nm)

Shape control of nanocrystals – platelets with 2D electronic structure

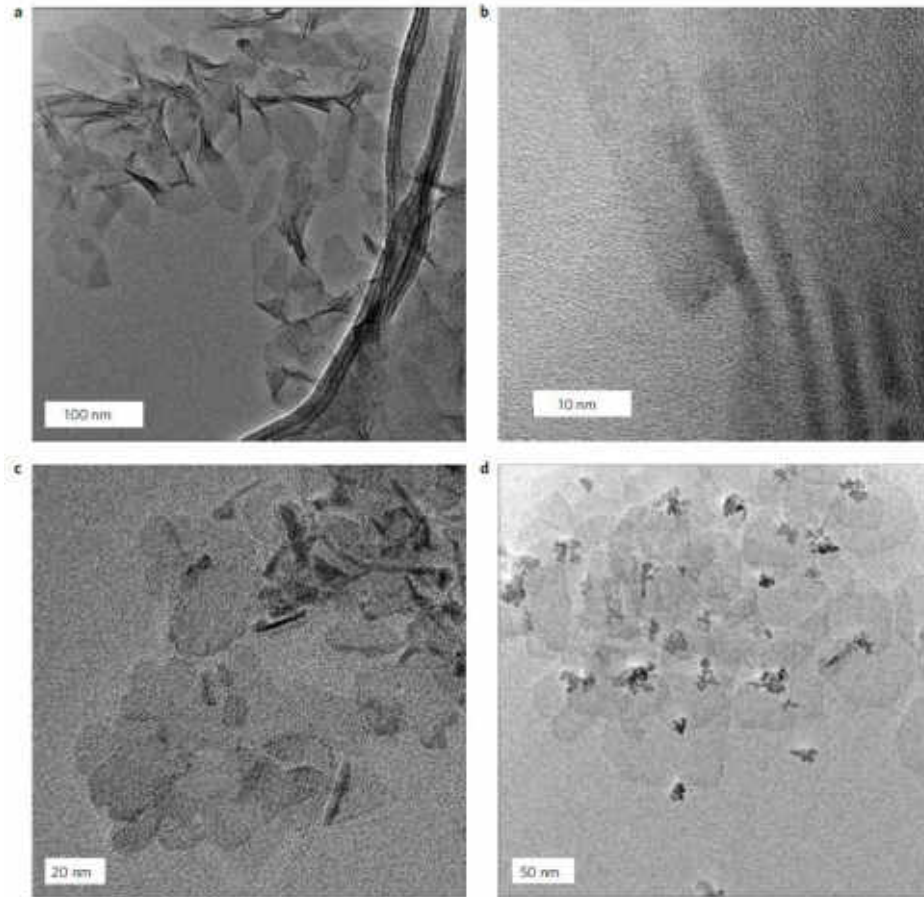


TEM images of nanoplatelets. a, Five-monolayer-thick CdSe NPLs. b, Six-monolayer-thick CdSe NPLs standing partly on their side. c, Six-monolayer-thick CdS NPLs. d, Six-monolayer-thick CdTe NPLs.

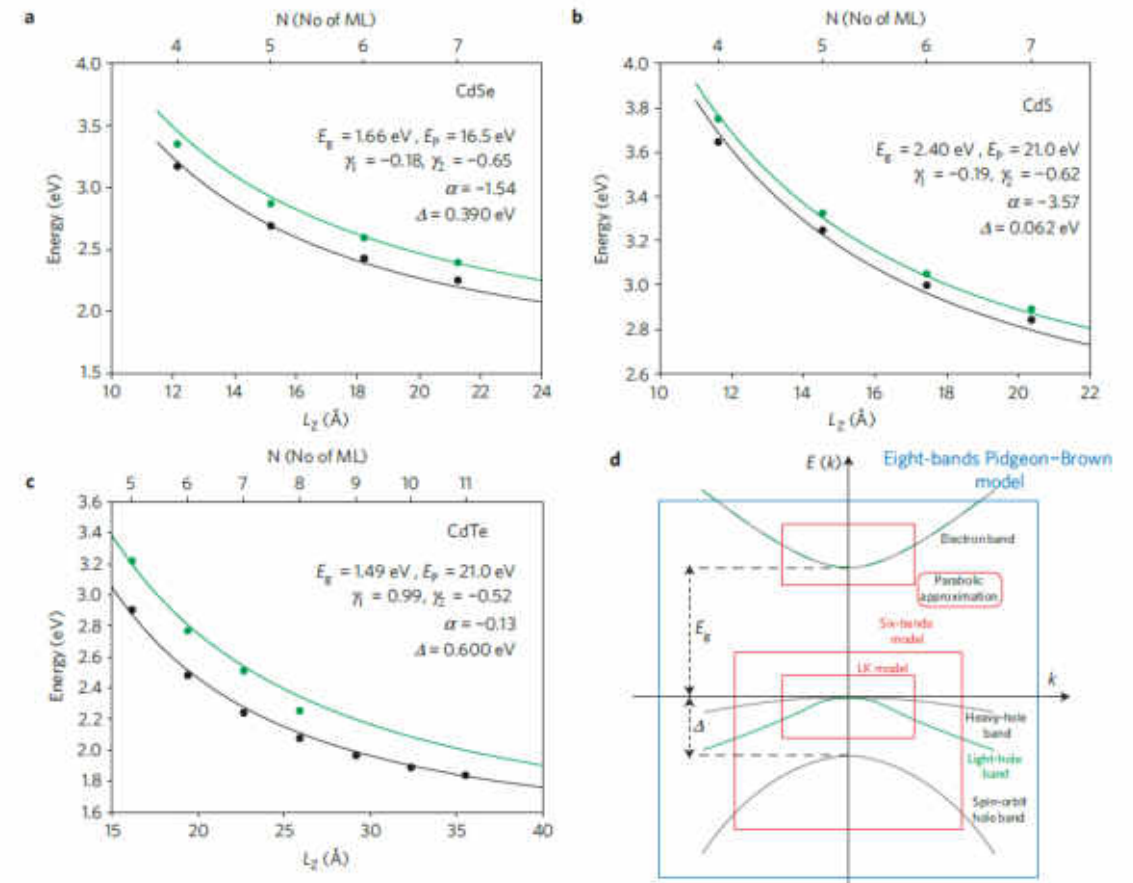

Energies of the electron/light-hole (green) and electron/heavy-hole (black) transitions versus the NPL thickness for CdSe (a), CdS (b) and CdTe (c). d, Schematic representation of the energy band structure in the vicinity of the 0-point of the Brillouin zone, as well as the validity domain of various band-structure models.

Timeline of luminescence performance enhancement

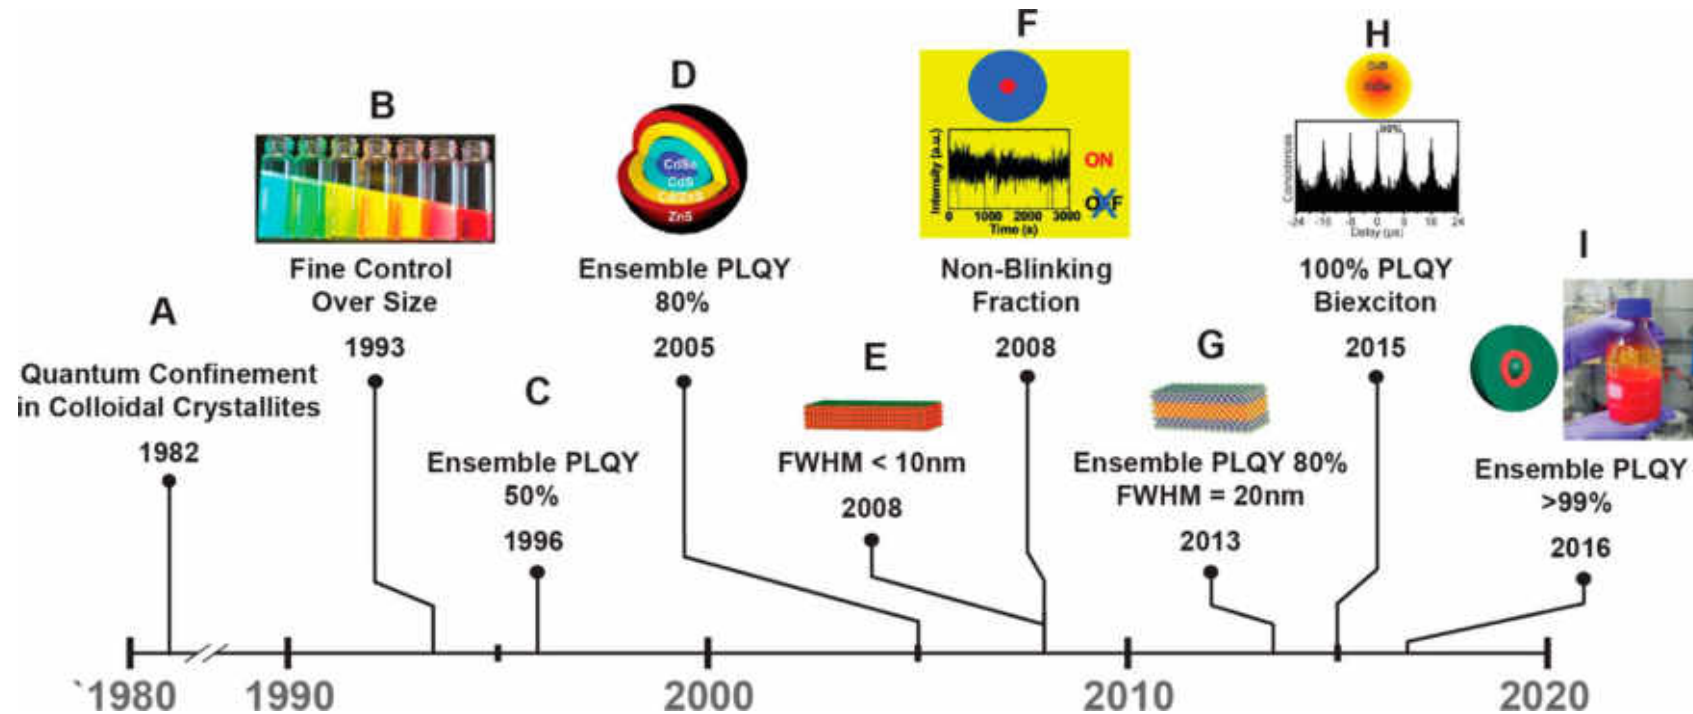

nature materials ARTICLES
PUBLISHED ONLINE: 9 FEBRUARY 2013 | DOI:10.1038/NMAT2729

Compact high-quality CdSe-CdS core-shell nanocrystals with narrow emission linewidths and suppressed blinking

Ou Chen¹, Jing Zhao², Vikash P. Chauhan³, Jian Cui¹, Cliff Wong¹, Daniel K. Harris¹, He Wei¹, Hee-Sun Han¹, Dai Fukumura², Rakesh K. Jain² and Moungi G. Bawendi^{1*}

High particle uniformity, high photoluminescence quantum yields, narrow and symmetric emission spectral line shapes and minimal single-dot emission intermittency (known as blinking) have been recognized as universal requirements for the successful use of colloidal quantum dots in nearly all optical applications. However, synthesizing samples that simultaneously meet all these four criteria has proven challenging. Here, we report the synthesis of such high-quality CdSe-CdS core-shell quantum dots in an optimized process that maintains a slow growth rate of the shell through the use of octanethiol and cadmium stearate as precursors. In contrast with previous observations, single-dot blinking is significantly suppressed with only a relatively thin shell. Furthermore, we demonstrate the elimination of the ensemble luminescence photobleaching that is an intrinsic consequence of quantum dot blinking statistical aging. Furthermore, the small size and high photoluminescence quantum yields of these novel quantum dots render them superior in vivo imaging agents compared with conventional quantum dots. We anticipate these quantum dots will also result in significant improvement in the performance of quantum dots in other applications such as solid-state lighting and illumination.

ACS NANO

Colloidal Spherical Quantum Wells with Near-Unity Photoluminescence Quantum Yield and Suppressed Blinking

Byeong Guk Jeong,¹ Young-Shin Park,^{1,2} Jun-Hyuk Chang,¹ Baun Cho,³ Jai Kyeong Kim,⁴ Heesuk Kim,⁵ Kookheon Cha,⁶ Jinhan Cho,⁷ Victor I. Klimov,⁸ Philip Park,^{9,10} Doh C. Lee,¹¹ and Wan Ki Bae^{1,11}

¹Department of Chemical and Biomolecular Engineering, KAIST Institute for the Nanocentury, Korea Advanced Institute of Science and Technology (KAIST), 291 Daejeon, Yuseong-gu, Daejeon 34141, Republic of Korea

²Chemistry Division, Los Alamos National Laboratory, Los Alamos, New Mexico 87545, United States

³Center for High Technology Materials, University of New Mexico, Albuquerque, New Mexico 87131, United States


⁴School of Chemical and Biological Engineering, The National Creative Research Initiative Center for Intelligent Hybrids, Seoul National University, 1 Gwanak-ro, Gwanak-gu, Seoul 151-747, Republic of Korea

⁵Department of Chemical and Biological Engineering, Korea University, 145 Ansan-ro, Seongbuk-gu, Seoul 02841, Republic of Korea

⁶Biomedical Hybrid Research Center, Korea Institute of Science and Technology (KIST), 1461 J. Hwang-ro, Seongbuk-gu, Seoul 02742, Republic of Korea

⁷Department of Chemistry and Biochemistry, University of California, Los Angeles, California 90095, United States

Colloidal QD research timeline illustrating evolution of nanostructure and luminescence performance.

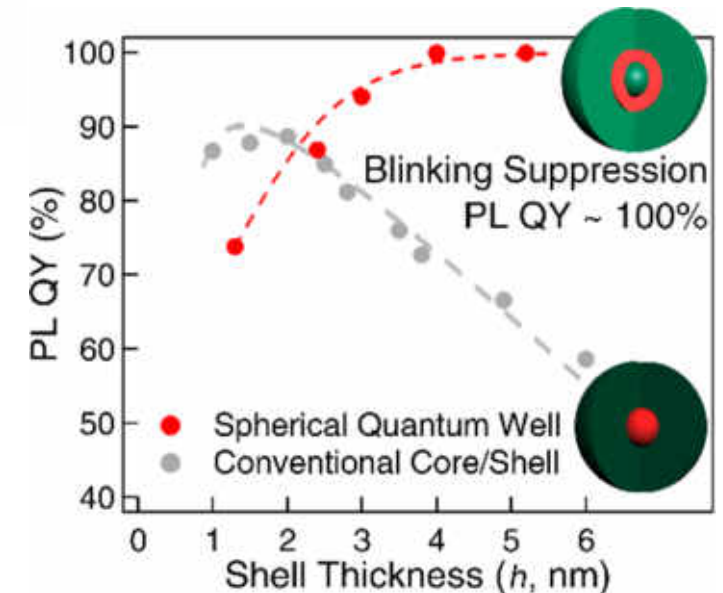

Expanding science and lessons learnt

Catalysis


Biological applications

Simple finding, report them early

Have colleagues to work on them

One useful application

Have industry adoption

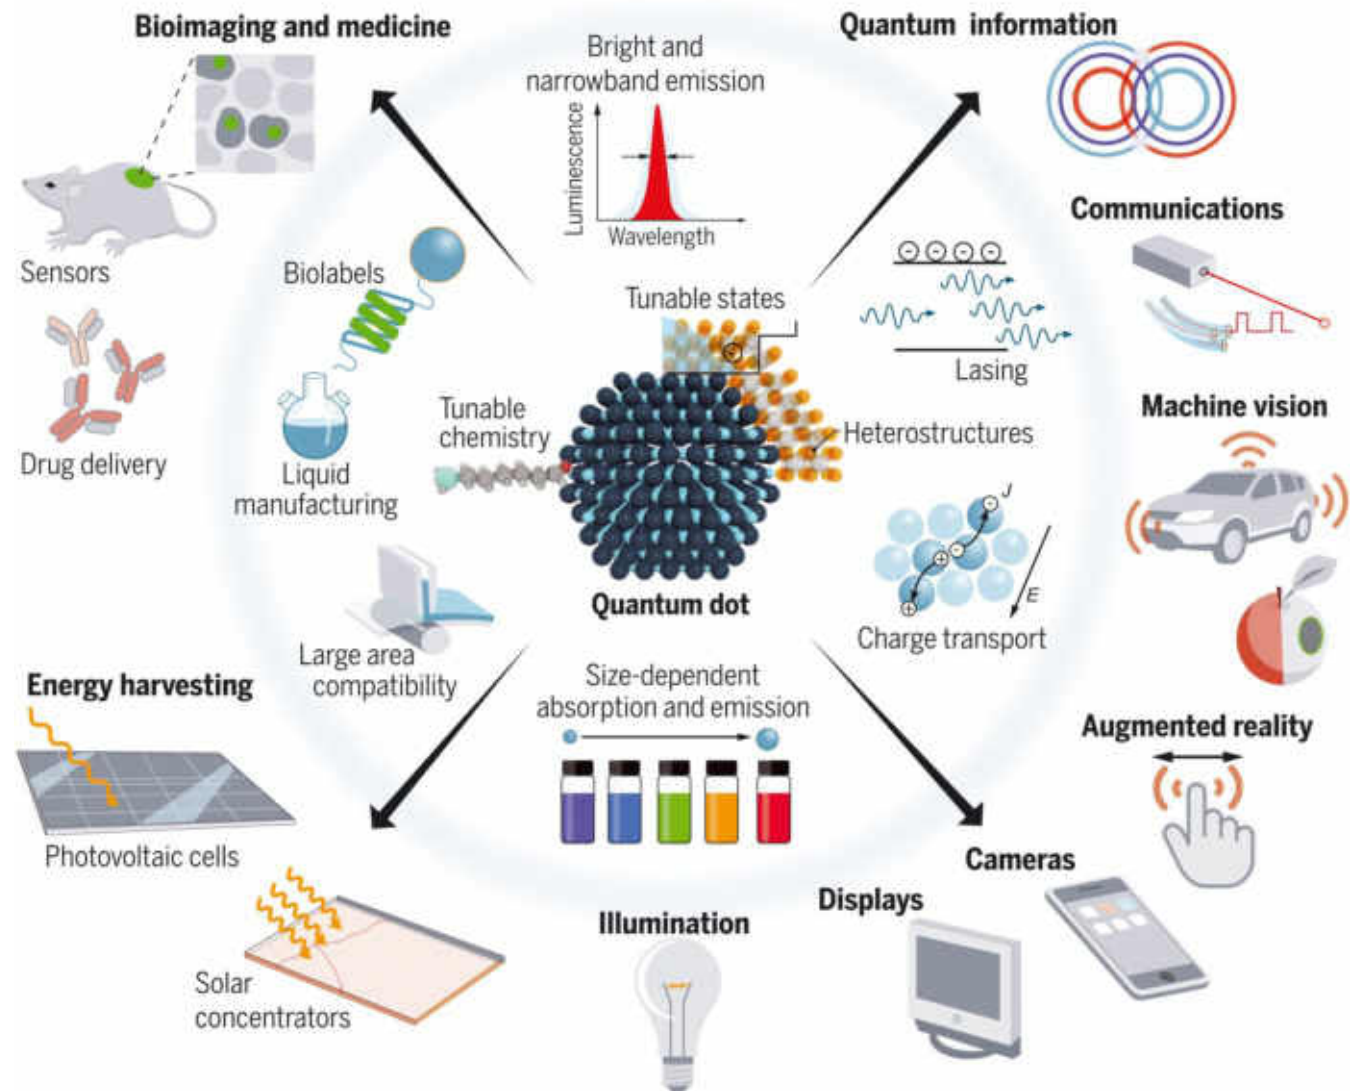

With Prof. Bawendi

